

- 23 **Keywords:** Ultra-high-performance seawater sea sand concrete, OPC replacement ratio, water-to-
- 24 binder ratio, strength, workability, shrinkage.

25 **1. Introduction**

26 Being the most widely utilized construction material, the demand for ordinary Portland cement
27 (OPC) concrete in infrastructure industries has significantly increased over the past few decades.
28 The total amount of cement produced worldwide in the year 2020 was 4.1 billion tons, which is
29 almost three-fold compared to the cement production in 1995 [1]. This huge demand and
30 consequently, the production, has not only exacerbated the scarcity of natural resources (i.e., fresh
31 water and river sand) by overexploiting them as raw materials but also worsened the ecological
32 balance through substantial CO₂ emission in the manufacturing of OPC [2]. An alternative to the
33 consumption of limited natural resources is to utilize seawater and sea-sand concrete (SWSSC)
34 which can be a sustainable substitute to depleting fresh water and river sand. In addition, proper
35 management of hazardous industrial by-products, including ground granulated blast furnace slag,
36 silica fume, fly ash, etc. is a potential challenge [3] with a noteworthy possibility of being reused
37 and recycled as supplementary cementitious materials (SCMs) in concrete manufacture. Blast
38 furnace slag and silica fume are by-products of steel and ferrosilicon manufacturing industries,
39 respectively [4], which possess pozzolanic reactivity and thus, may be used as SCMs by replacing
40 OPC in SWSSC. However, concerns remain with the use of chloride enriched marine resources in
41 concrete as this can potentially stimulate corrosion in the embedded reinforcing steel. Alternative
42 hybrid construction approaches utilizing seawater and sea-sand concrete and corrosion resistant
43 materials such as fiber reinforced polymers (FRP) and stainless steel, nonetheless, possess an
44 enormous potential in future sustainable construction practice e.g., [5-9], particularly in the coastal
45 regions.

46 Relevant studies have demonstrated that the utilization of sea-sand [2, 10] and seawater [11-13] in
47 concrete increases early-age compressive strength, lowers long-term compressive strength [14,

48 15], makes the concrete less workable [16], and increases drying shrinkage [17, 18] compared to
49 fresh water and river sand counterparts due to the salt and sea-shell contents present in them.
50 Application of seawater to cure SWSSC reduces the compressive strength and modulus of
51 elasticity as opposed to conventional freshwater curing [15]. The expansion of SWSSC because of
52 alkali-silica reaction (ASR) which ultimately induces cracking in concrete can be substantially
53 mitigated by utilizing SCMs (i.e., blast furnace slag, fly ash, silica fume etc.) [19]. Hence,
54 utilization of such by-products from manufacturing industries can mitigate the concrete reactivity
55 concerns and thus advocate sustainability in current construction practice.

56 Ultra-high-performance concrete (UHPC) has recently emerged as an efficient alternative to
57 normal strength concrete due to its superior mechanical and excellent durability characteristics,
58 with high demand in infrastructures designed for long service life. According to some available
59 literature, UHPC is a new generation concrete that possesses an ultra-high strength of at least
60 120 MPa [20, 21]. UHPC is defined by its relatively high binder content and significantly lower
61 water-to-binder ratio compared to conventional concrete. Enhancement of microstructure,
62 improvement of homogeneity, acceleration of hydration reactions, toughness improvement, and a
63 significant reduction in porosity are the key manufacturing principles of UHPC [22, 23]. Uniform
64 and dense microstructure and improved interfacial transition zone (ITZ) lead to the superior
65 performance of UHPC compared to conventional concrete. Utilization of SCMs [22, 24] and use
66 of water reducing superplasticizers particularly containing polycarboxylates [25] helps to achieve
67 superior strength and maintain workability even though the water-to-binder ratio is kept relatively
68 low. High binder content and use of superplasticizers in UHPC produces high heat during
69 hydration and causes higher shrinkage strains, which is the prime reason behind its susceptibility
70 to cracking [24, 26]. The portion of autogenous shrinkage is significantly larger in UHPC than

71 normal concrete due to the presence of high binder content and a very low water-to-binder ratio.
72 Partial replacement of mixing water by crushed ice [27], applying heat curing [23], limiting the
73 dosage of superplasticizer [26], and incorporation of super absorbent polymers [28], etc. are some
74 innovative approaches to mitigate shrinkage in UHPC.

75 The above-mentioned papers on UHPC mainly dealt with concrete using fresh water and river
76 sand. Natural and artificial seawater, as well as sea sand, have been successfully used in the
77 preparation of ultra-high-performance concrete which achieved satisfactory mechanical
78 characteristics [29]. In consideration of the review above, there is a lack of research on the strength,
79 workability, and shrinkage of ultra-high-performance seawater and sea sand concrete (UHP-
80 SWSSC), OPC-slag based UHP-SWSSC, let alone the influence of OPC replacement ratio on the
81 strength, workability, and dimensional stability (e.g., volumetric change of concrete due to
82 shrinkage). This paper explores the possibility to develop a UHP-SWSSC from local marine
83 resources in Australia which utilize industrial by-products such as blast furnace slag and silica
84 fume to replace OPC. Several mixes were prepared by varying the cement replacement ratio (0%
85 as the control mix, 25%, 37.5%, 50%, and 62.5%), aggregate type, and water-to-binder ratio. The
86 impact of these parameters on the compressive strength and workability was assessed. UHPC with
87 a similar mixing ratio but utilizing tap water and river sand as well as washed Sydney beach sand
88 were prepared and analyzed to compare with the seawater and sea sand UHPC. The influence of
89 different types of aggregates, cement substitution ratio, and water-to-binder ratio on early age and
90 long-term shrinkage properties of UHPC was determined. Finally, an appropriate UHP-SWSSC
91 mix was selected based on its physical, mechanical, and dimensional stability characteristics.

92 **2. Raw Materials, Mix Proportions, and Methods**

93 **2.1. Raw Materials**

94 A general-purpose ordinary Portland cement conforming to AS 3972-2010 [30] was used in this
95 study with two supplementary cementitious materials (SCMs) – ground granulated blast furnace
96 slag (GGBFS) and undensified silica fume conforming to AS 3582.2-2016 [31] and
97 AS/NZS 3582.3-2016 [32], respectively. The slag was sourced from Australian Steel Mill Services
98 (ASMS), Port Kembla, NSW, and the silica fume was sourced from Simcoa, plant Kemerton,
99 Western Australia. Chemical oxide compositions of the binders (**Table 1**) were determined by X-
100 ray fluorescence (XRF) spectroscopy in an AXIOS WDXRF instrument and SUPERQ software
101 was used for data analysis.

102 *[Table 1 near here]*

103 Natural seawater and sea sand were collected from Malabar beach of Sydney, NSW, Australia for
104 fabricating UHPC. The cations and anions in seawater were detected through inductively coupled
105 plasma – optical emission spectrometry (ICP-OES) and ion chromatography (IC), respectively.
106 **Table 2** compares the ion concentrations of the natural seawater used in this study with that of the
107 world average values [29]. The seawater collected from Malabar beach was found to be reasonably
108 close to the corresponding world average values. Tap water was used in mixing and curing of tap
109 water river sand and tap water washed Sydney beach sand UHPC.

110 *[Table 2 near here]*

111 *[Figure 1 near here]*

112 The sea sand was sieved through a 1.18 mm sieve to separate the stones, seashells, organic
113 materials, and other impurities such as portions of aquatic plants, branches, man-made pollutants,
114 etc., as per Willie and Boisvert-Cotulio [33] recommendations. The processed sand is presented in
115 **Figure 1**. The total mass of impurities was 2.85% of the natural sea sand. Natural river sand was
116 obtained from Taren Point, New South Wales. The washed beach sand was collected from beaches
117 outside Sydney and washed thoroughly with fresh water to make it salt-free. Particle size
118 distribution of different sands determined according to AS 1141.11.1-2009 [34] are compared in
119 **Figure 2**. Sea sand with and without impurities is termed as ‘sea sand before processing’ and ‘sea
120 sand after processing’, respectively. Natural river sand was found to be well graded, while the sea
121 sand was gap graded with a significant portion of its particles retaining on 0.3 mm and 0.6 mm
122 sieves. To avoid any effect of aggregate gradation in this study, natural river sand with the same
123 particle size distribution as the sea sand was used. This modified river sand is termed as ‘processed
124 river sand’ in this study. Modification of the sea sand by eliminating larger-sized particles does
125 not alter its particle size distribution. The fineness of sea sand was found to be in between washed
126 Sydney beach sand and natural river sand.

127 *[Figure 2 near here]*

128 The chemical composition of the sands was determined using the X-ray fluorescence (XRF)
129 spectroscopy technique and presented in **Table 3**. It is evident that the sands are rich in silica.
130 **Table 4** lists various physical properties of the sands used in this study including particle densities
131 (i.e., oven-dry density, saturated surface dry or SSD density, apparent density), bulk densities
132 (uncompacted and compacted), percentage of water absorption, and percentage void determined
133 following relevant standards [35-37]. Natural river sand was found to possess slightly higher oven
134 dry as well as SSD particle density compared to marine sands, due to the presence of a bigger

135 proportion of larger-sized aggregates (especially over 1.18 mm) in natural river sand and light-
136 weight sea-shell fragments in sea sand. Water absorption of sea sand is the highest (3.46%),
137 whereas natural river sand has the lowest water absorption (1.68%). Difference between the
138 uncompact and compacted bulk density was found to be higher in natural river sand, because of
139 the presence of aggregates with various size ranges. Percent voids were measured to be very similar
140 among different sand types (ranging between 39 – 41%).

141 The surface morphology of different sand particles and SCMs were assessed through SEM
142 micrographs as shown in **Figure 3**. The procedure for microstructural analysis is discussed in
143 **Section 2.3.3**.

144 *[Figure 3 near here]*

145 *[Table 3 near here]*

146 MasterGlenium SKY 8700, a polycarboxylate-based high range water reducer (HRWR)
147 conforming to the requirements of AS 1478.1 [38], was used for batching UHP-SWSSC for its
148 excellent cement dispersion and slump retention ability along with its suitability to be used with
149 self-compacting concrete.

150 *[Table 4 near here]*

151 **2.2. Mix Proportions, Batching, and Specimen Preparation**

152 A total of 12 UHPC and one normal strength concrete mixes summarized in **Table 5** were
153 investigated in this study. No steel fiber was added to the UHPC in order to produce an
154 economically viable mix and eliminate the chances of steel corrosion. Seven UHPC mixes were
155 prepared with seawater and sea sand (UHP-SWSSC), two from washed Sydney beach sand and

156 tap water (UHP-TWWBSC), and the remaining three utilized river sand and tap water (UHP-
157 TWRSC). Five mix ratios with varying proportions of OPC replacements were chosen for UHP-
158 SWSSC. UHP-SWSSCC with 100% OPC (termed as ‘control mix’) along with 25%, 37.5%, 50%,
159 and 62.5% of OPC replacement by ground slag and silica fume were produced. The control mix
160 was developed based on the recommendations provided by Willie and Boisvert-Cotulio [33] and
161 through a trial-and-error process until a suitable mix with satisfactory flowability and strength was
162 achieved. Although the ratio of OPC to supplemental material (ground slag in this study) is
163 suggested to be 1:0.25 by weight in [33], this study explores the possibility to utilize slag at a much
164 higher proportion (up to a ratio of OPC: slag = 1:1.33). In the OPC replaced mixes, the portion of
165 silica fume was kept constant at 12.5% of the total binder (except OPC-slag binary mix with 25%
166 substitution of OPC). Total binder content, aggregate content, water-to-binder ratio, and
167 superplasticizer-to-binder ratio were kept the same for all the mixes with different OPC
168 replacements (1200 kg/m³, 1000 kg/m³, 0.2, and 0.02, respectively). Two more seawater and sea
169 sand UHPC mixes were prepared by altering the water-to-binder ratio (0.15 and 0.25) of the 50%
170 OPC replaced mix. **Table 5** also presents the label for each of the concrete mixes (termed as ‘mix
171 ID’); each label consists of the type of aggregate used, percentage of OPC replacement, and water-
172 to-binder ratio. For example, a mix ID of SS-50-0.2 refers to the UHPC mix where sea sand has
173 been used as aggregate, with an OPC substitution of 50% and a water-to-binder ratio of 0.2.

174 *[Table 5 near here]*

175 For batching, the cement, SCMs and SSD fine aggregate were dry mixed for ten minutes at low
176 speed (50 rpm) in a laboratory pan mixer capable of controlling mixing speed. Water and HRWR
177 were mixed separately as per admixture supplier recommendations and later added to the dry
178 materials over 30 seconds. Afterward, mixing was continued for an additional 8 minutes at low

179 speed and another 2 minutes at medium speed (100 rpm) until a workable mix was attained. UHPC
180 prepared in this study was found to be highly flowable and self-compacting, except for the mixes
181 with significant OPC replacement and a very low water-to-binder ratio (particularly, SS-50-0.15).
182 Immediately after mixing, the flow spread of the fresh UHPC was measured on a flow table as per
183 ASTM C1437-15 [39] guidelines and the fresh density was measured following procedures
184 outlined in ASTM C 138 [40]. According to the relevant standard [21], the flow table test was
185 modified to adjust to UHPC's fluid nature. Concrete was poured into a mold in a single layer
186 without tamping, the table was not dropped, and the fresh concrete was allowed to flow. The
187 diameter of the flow spread was measured and reported. Simultaneously, standard
188 50 mm × 50 mm cube specimens were prepared and compacted on a vibrating table running at low
189 frequency. The molds were then stored in a temperature and moisture-controlled cabinet at 23°C
190 and relative humidity of 50% for 24 ± 2 hours. After the specified time, the concrete specimens
191 were demoulded, and water cured. Two sets of specimens from each mix were prepared; one set
192 was cured in a 23°C lime-saturated water bath while the other was cured in natural seawater at the
193 same temperature. A set of 25 mm × 25 mm × 285 mm prisms were also prepared from each batch
194 to monitor UHPC's shrinkage behavior.

195 **2.3. Testing Procedures**

196 **2.3.1. Heat of hydration**

197 The heat evolved in the first 72 hours of hydration of some representative UHPC pastes was
198 captured in a TAM Air isothermal calorimeter operating at 23°C. From **Table 5**, the paste portion
199 of SS-0-0.2, RS(P)-0-0.2, and SS-50-0.2 were chosen for the test to evaluate the effects of seawater
200 and SCM on the reaction kinetics of UHPC. For this purpose, about 12 g paste sample was hand-
201 mixed in a 20 ml glass ampoule and sealed before quickly transferring the specimen along with an

202 inert reference sample (oven-dried quartz sand) in the calorimeter chambers. Each reference
203 sample mass was determined to have the same heat capacity as the UHPC paste sample. The time
204 elapsed between the addition of the mix water and the start of the test was adjusted during data
205 analysis. Each test was replicated to confirm the repeatability of the method.

206 *2.3.2. Mechanical properties and shrinkage*

207 For each mix proportion and curing condition studied, the 1, 3, 7, 28, and 90 days compressive
208 strength of 50 mm × 50 mm cube specimens were determined following the requirements of
209 ASTM C109/C109M-2020 [41]. Meanwhile, length change of prism specimens was measured up
210 to an extended period of 120 days to determine the long-term drying and autogenous shrinkage of
211 UHPC. The total shrinkage samples were air-dried after demoulding in a moist chamber at a
212 constant conditioning temperature of 23°C and 50% relative humidity while the autogenous
213 shrinkage samples were properly sealed with aluminum tape to prevent any loss of moisture and
214 thus obtain their autogenous shrinkage at the same temperature and relative humidity. The total
215 and autogenous shrinkages were determined by measuring the length change of the specimens
216 according to AS 1012.13-2015 [42]. Drying shrinkage was determined from the difference
217 between the respective total shrinkage and autogenous shrinkage.

218 *2.3.3. Microscopic imaging*

219 A Hitachi S3400 scanning electron microscope (SEM) was utilized for investigating the
220 microstructure of 28 days mature UHPC. For this purpose, about 5 mm thick slices of samples
221 were cut using a slow-rotating diamond saw. Specimens were immersed in 100% ethyl alcohol to
222 stop the hydration and impurities were eliminated by ultrasonic cleansing. The imaging surface of
223 the specimens was gold coated in an Emitech K550x gold sputter coater. For imaging raw binders
224 and sands, the particles were attached on an adhesive carbon tape and gold coated. The accelerating

225 current for imaging was set at 30 amps with a beam strength of 20 kV and a working distance of
226 approximately 5 mm under a high vacuum mode. Images of the microstructure were captured using
227 the backscattered electron (BSE) mode of the electron microscope.

228 **3. Results and Discussions**

229 ***3.1. Heat of Hydration***

230 The heat evolution in the first 72 hours of cement hydration (normalized per unit mass of cement)
231 in the presence of tap water, seawater, and SCMs (slag and silica fume) is illustrated in **Figure 4**.
232 The typical stages of cement hydration such as the dissolution of cement particles as identified in
233 the initial peak right after the addition of water, induction peak, and the acceleration peak marking
234 the hydration of cement [43] are observed in **Figure 4(a)**. The temporal change in the occurrence
235 of the acceleration peak suggests that seawater accelerates cement hydration. The acceleration
236 peak shifts by at least 6-8 hours from seawater hydration of cement along with reaching about 15%
237 higher heat flow. A similar phenomenon is also observed when 50% cement is replaced by 37.5%
238 slag and 12.5% silica fume. However, the mechanism behind them is different.

239 *[Figure 4 near here]*

240 When seawater is utilized in the mix, the abundance of chloride ions chemically binds with the
241 calcium, aluminate, and ferrous phases of cement [44], forming insoluble calcium oxychloride
242 phase and Friedel's salt [45]. When SCMs replace 50% of cement, it causes a similar effect, but
243 from the well-explored filler effect [46, 47]. The slag and silica fume particles act as fillers between
244 cement particles and offer extra nucleation sites for hydration products to occupy [46, 47]. As
245 such, the heat evolved per unit mass of cement is higher than cement-only paste. This is also
246 reflected in **Figure 4(b)** which shows a significantly higher cumulative heat generated per unit

247 mass of cement confirming the filler effect of SCMs. The heat of hydration of cement from
248 seawater and tap water mixing after 72 hours of hydration is somewhat similar, but seawater
249 mixing generates more heat in between 12-30 hours. Thus, it is expected that the 1-day strength of
250 seawater composite could exceed that of tap water, however, may follow a similar strength
251 development in later ages of hydration.

252 **3.2. Properties of Fresh Concrete**

253 The fresh and 28 days SSD density of UHPC are summarized in **Table 6**. The SSD density of
254 concrete was found to be greater than its fresh density for all the mixes due to the continuing water
255 absorption during the curing period. UHPC was found to possess around 6.6% greater unit weight
256 than normal strength concrete because of its significantly compact microstructure from the
257 selection of lower water-to-binder ratio [48]. The unit weight of seawater sea sand UHPC was
258 found to be marginally higher than tap water river sand and washed beach sand UHPC, for both
259 100% OPC and 50% OPC replaced mix. However, when sea sand is replaced with washed beach
260 sand and river sand, the fresh densities drop by 0.35% and 0.9%, respectively. The use of seawater
261 may have resulted in the slight increase in density from the formation of more hydration products
262 as captured in the heat evolution curves in **Figure 4**.

263 *[Table 6 near here]*

264 The incorporation of SCMs reduced the unit weight of UHPC, possibly due to the lower densities
265 of SCM compared to OPC. The percentage of OPC replacement has been found to have a linear
266 relationship with the decrease in a unit weight of both fresh and 28-day SSD unit weight. From
267 **Table 6**, an OPC replacement of 25%, 37.5%, 50% and 62.5% yielded in a reduction of 1.15%,
268 3.49%, 3.99% and 4.01%, respectively in the unit weight of fresh UHP-SWSSC. The incorporation

269 of silica fume had a greater effect on unit weight reduction compared to ground slag, due to the
270 significantly lower relative density of silica fume than cement and slag used in this study. These
271 findings are consistent with previous studies of Zain et al. [48] and Turk [49].

272 The UHPC mixes reported in **Table 5** were trialed to possess excellent workability in general;
273 their flow spread is summarized in **Figure 5**. The high flowability was achieved due to the
274 utilization of polycarboxylate-based superplasticizer at a relatively high dosage than recommended
275 for normal grade concrete. Regardless, the effects of slag, silica fume, and the use of different
276 types of sand on the flowability can still be comparatively assessed. In general, the presence of
277 ground slag decreased the flowability of all UHPC mixes. For instance, a 12.5% reduction in the
278 flow spread resulted from the 25% replacement of cement with slag (**Figure 5(a)**). The angular
279 shape of slag particles (shown in **Figure 3(d)**) together with the accelerated calcium reaction is
280 possibly the primary reason behind the reduced flowability. However, the workability of UHPC
281 improved when silica fume was added in addition to slag as partial replacements of OPC. The
282 ternary blends produced better workability compared to the OPC-slag binary blend from the ‘ball
283 bearing’ and lubricating effect of the spherical silica fume particles, as demonstrated in **Figure 3(e)**
284 [50-52]. The addition of 12.5% silica fume in SS-37.5-0.2 increased the flow spread by 12.7%
285 compared to the OPC-slag binary mix. However, with the increase of slag content in ternary
286 blends, the flow degraded. The SS-62.5-0.2 mix with 50% ground slag and 12.5% silica fume
287 yielded a 19.4% lower flow spread compared to the control mix. This particular mix was viscous
288 and required high-frequency vibration for proper compaction.

289 *[Figure 5 near here]*

290 From **Figure 5(b)**, the flowability of UHPC slightly declined from the use of sea sand and
291 seawater. The uniformity and size fractions of sea sand particles together with the presence of
292 irregularly shaped seashells and other micro-impurities may have led to a reduced flow [2].
293 **Figure 3** confirms that washed beach sand particles are round in shape with a relatively smooth
294 surface, while the river sand particles are mostly angular with rough edges and varying size
295 fractions. The angularity and roughness of sea sand somewhat lie in between the washed beach
296 sand and river sand, which is also reflected in the flowability of UHPC ranging in the same order.
297 It is evident from **Figure 5(b)** that the control UHP-SWSSC mix had a flow spread of 360 mm, in
298 contrast to 390 mm and 345 mm for washed Sydney beach sand and processed river sand UHPC
299 with identical mix proportions. The 50% OPC replaced mixes also showed a similar trend.

300 In addition, the flow spread increased with the increase in the water-to-binder ratio, as expected
301 (**Figure 5(c)**). 50% OPC replaced UHP-SWSSC with a water-to-binder ratio of 0.15, 0.2, and 0.25
302 produced slump spreads of 185 mm, 340 mm, and 360 mm, respectively. The SS-50-0.15 mix was
303 found to be highly viscous, and the workability was challenged in specimen making; this also
304 yielded a 45.6% reduced spread compared to the SS-50-0.2. Chen et al. [53] reported that UHPC's
305 extremely low water content is insufficient to fill the inter-particle void spaces and is readily
306 absorbed around the particle surfaces while leaving the voids empty. This study found a water-to-
307 binder ratio of 0.2 to be optimum for lubrication of the granular materials at a superplasticizer dose
308 of 24 kg/m³. Overall, the workability of all the UHPC mixes in this study was found to be similar
309 in comparison with the targeted 280 mm – 340 mm flow spread of Willie and Boisvert-Cotulio
310 [33]. The results are also consistent with the flowability of seawater and sea sand UHPC studied
311 by Teng et al. [29].

312 **3.3. Compressive Strength**

313 **Table 7** summarizes the compressive strength of all mixes investigated in this study under both
314 tap water and seawater curing regimes; the results are the mean of the strength of three identical
315 specimens. The strength of conventional concrete cylinders under tap water curing was also
316 assessed for comparison purposes. The 1-day strength was determined just after demoulding of
317 specimens and before storing them in the curing chamber. The standard deviation is well within
318 5% of the compressive strength value, which indicates lesser variability and better homogeneity
319 of respective UHPC mixes. The following section highlights the influence of several mix
320 proportion parameters on the compressive strength of UHPC.

321 *[Table 7 near here]*

322 **3.3.1. Effect of seawater and sea sand**

323 **Figure 6** shows the comparative compressive strength development of UHPC composed of
324 different types of sand and mixing water under tap water curing conditions. The incorporation of
325 sea sand and seawater in UHPC can produce relatively higher compressive strength at an early
326 age, particularly, up to 28 days. The control mix SS-0-0.2 in this testing regime yielded
327 substantially high early-age strength, with no cement replacement. However, comparative
328 discussion can be made for the other mixes in which, the sand type is the only variable. Among
329 the 50% OPC substituted mixes, the seawater and sea sand mix (SS-50-0.2) produces 29.1%,
330 16.8%, and 13.9% larger compressive strength values in comparison with tap water and washed
331 beach sand mix after 1, 3, and 7 days, respectively. Although in the early ages, the difference is
332 more pronounced, the long-term (90 days) strength of all mixes is similar. The seawater and sea
333 sand mix reached 62.5% of its 90-day strength at an age of only 3 days, whereas the river sand and
334 washed beach sand mixes utilizing tap water in mixing achieved slightly over half of their long-

335 term strength at three days. This indicates that seawater accelerates the hydration of the binder,
336 providing early-age strength gain to UHPC. This is also reflected in the heat of hydration curves
337 in **Figure 4** which shows greater heat release from the use of seawater. For tap water mixing, the
338 hydration continues beyond 28 days, although at a slower pace, but reaches a similar strength as
339 that of seawater mixed UHPC. The higher early-age compressive strength is due to the abundance
340 of chloride content in sea sand and seawater which accelerates the hydration reaction initially.
341 Faster hydration generates a greater amount of hydration products, such as calcium silicate hydrate
342 (C-S-H), which blocks the pores in the resulting concrete and thus enhances the early strength
343 development [2, 16].

344 *[Figure 6 near here]*

345 However, the development of strength gain in UHP-SWSSC slows down with time, especially
346 after 28 days. The UHP-SWSSC mix with 50% cement substitution (SS-50-0.2) yields the highest
347 strength of 136.8 MPa after 28 days of tap water curing, which is a mere increase (6% and 2.2%,
348 respectively) compared to UHP-TWWBSC and UHP-TWRSC counterparts. Similar trends were
349 also observed when mixes were cured in a seawater environment. This deterioration in strength
350 gain occurs as a result of leaching out of soft hydration products with time [11, 14]. Long-term
351 strengths, especially after 90 days of curing were found to be almost identical, which aligns with
352 the findings of the studies of Mohammed et al. [12]. Overall, a slight increase in the early age
353 strength and a slight reduction in the long-term strength of SCM-based UHP-SWSSC were
354 consistent with the results of Teng et al. [29].

355 3.3.2. *Effect of OPC replacement by ground slag and silica fume*

356 It is apparent from **Figure 7** that in general, UHPCs produce significantly higher strength (about
357 4 times) than normal strength concrete with a water-to-binder ratio of 0.35. The ratio of strength
358 between OPC-based UHPC and NC was found to be higher at an early age (a strength ratio of 4.7
359 after 1-day), whereas a slightly reduced strength ratio of 3.4 has been found for long-term 90-day
360 compressive strength. This indicates the faster development of strength in UHPC with high binder
361 content at a significantly lower water-to-binder ratio.

362 *[Figure 7 near here]*

363 It has been found that early-age strength decreases with the increase in OPC replacement. UHPC
364 with no cement replacement yielded a compressive strength of 85.2 MPa at day 1, whereas 25%,
365 37.5%, 50%, and 62.5% OPC replaced mixes produced respectively 57 MPa, 38.9 MPa, 37.3 MPa,
366 and 22.9 MPa strength at the same age. OPC substitution by SCMs, such as silica fume and ground
367 slag, was found to yield lower strength initially, up to as early as 7 days of casting. The slower rate
368 of pozzolanic reaction of ground granulated blast furnace slag at room temperature curing hinders
369 the early age strength development [54]. However, OPC substituted mixes tend to generate more
370 strength compared to cement-based mixes as time goes on, especially after 28 days of curing and
371 beyond. In our study, 28-days, as well as 90-days strengths of all UHP-SWSSC mixes, were found
372 to be quite similar, with a slight increase of strength for higher OPC replacements. For example,
373 the 50% OPC replaced mix reaches a compressive strength of 136.8 MPa after 28 days of tap water
374 curing, while the 100% OPC variant has a slightly lower strength of 127.4 MPa. The strength ratios
375 of 62.5% cement replaced mix to control mix were 0.27, 0.71, 0.95, 1.03, and 1.05 after tap water
376 curing periods of 1, 3, 7, 28, and 90 days correspondingly. The short-term strengths were
377 considerably lower in comparison with the control mix, while slightly higher long-term strengths

378 were observed. Silica fume with significantly smaller particle size has a filler effect which
379 improves the particle packing density. The highly pozzolanic slag and silica fume convert the
380 $\text{Ca}(\text{OH})_2$ into secondary C-S-H and thus enhance the interfacial bond, which eventually leads to
381 more homogeneous ITZ and therefore, an increased strength [54, 55]. Overall improvement of
382 microstructure in SCM incorporated UHPC blends enables them to achieve higher strength
383 compared to OPC based UHPC.

384 *[Figure 8 near here]*

385 UHP-SWSSC mixes with different proportions of cement replacement show identical trends when
386 cured under a seawater environment (**Figure 8**). The mix with 50% OPC replacement yields 56.3%
387 and 24.9% lower strength after 1 and 3 days of curing compared to the control mix, however it
388 generates 10.8% and 7.5% higher strength after a curing period of 28 and 90 days, respectively.

389 *3.3.3. Effect of water-to-binder ratio*

390 Three mixes of 50% cement replaced UHP-SWSSC were compared with varying water-to-binder
391 ratios, i.e., 0.15, 0.2, and 0.25. In general, an increase in the water-to-binder ratio causes a
392 reduction in compressive strength (**Figure 9**). This result is consistent with the findings of Zhang
393 and Zhang [56], where it was found that the reduction of water content in the UHPC matrix
394 densifies the hydration film produced around the surface of cementitious particles, which prohibits
395 further hydration reaction. Additionally, lowering the water-to-binder ratio reduces the porosity in
396 microstructure, which eventually leads to greater strength. However, early age strength was seen
397 to be impacted more compared to long-term strength. Increasing the water-to-binder ratio from
398 0.15 to 0.25 reduces the 1-day and 3-days strength by 59.8% and 20.2%, whereas the strength
399 reductions were found to be 6.4% and 3.5% after 28 and 90 days, respectively.

400 *[Figure 9 near here]*

401 Interestingly, the SS-50-0.2 mix with a water-to-binder ratio of 0.2 yielded marginally higher 28-
402 day strength compared to the counterpart SS-50-0.15 with a lower water-to-binder ratio. In the
403 case of extremely low water content, the available water is completely absorbed within the particle
404 surfaces, thereby leaving the voids empty. If the water content in the cementitious matrix is lower
405 than a minimum margin, the strength does not increase due to the void spaces present in the
406 microstructure and due to the unavailability of water for hydration of cement particles [53, 56].
407 The UHPC mix with a very low water-to-binder ratio of 0.15 was found to be sticky and viscous,
408 with a flow spread of only 185 mm (**Figure 5(c)**). The cross-section exhibited visible air voids as
409 shown in **Figure 10(a)**, which could not be eliminated through vibration. The porous
410 microstructure with an extremely low water-to-binder ratio inhibits its ability to gain long-term
411 ultra-high strength. In contrast, cross-sections of SS-50-0.2 and SS-50-0.25 mixes were more
412 homogeneous with almost no visible air voids, as shown in **Figure 10(b)** and **Figure 10(c)**. The
413 optimum water-to-binder ratio in order to achieve maximum long-term compressive strength was
414 found to be 0.2.

415 *[Figure 10 near here]*

416 3.3.4. *Effect of curing condition*

417 The influence of seawater curing on the compressive strength of UHPC comprised of different
418 aggregates is depicted in **Figure 11** and **Figure 12**. Overall, seawater incorporated as curing water
419 has a negative impact on the strength of UHPC. The 100% OPC-based UHP-SWSSC samples
420 cured in tap water yielded higher strength compared to curing in seawater, 3.3%, 8.8%, 13.5%,
421 and 13.8% strength enhancement after curing periods of 3, 7, 28, and 90 days, respectively

422 **(Figure 11)**. River sand and washed Sydney beach sand-based UHPC experienced similar
423 deterioration in strength while cured in seawater, with 8.67% and 9.31% of reduction, respectively
424 after a prolonged seawater curing period of 90 days. The loss of strength in seawater-cured cement-
425 based UHPC has been observed to escalate with the curing age. The degradation of strength gain
426 may have occurred because of the formation of expansive (such as ettringite and Friedel's salt) as
427 well as soft leachable compounds in the cementitious microstructure due to seawater penetration
428 during prolonged exposure [14]. Development of micro-cracks due to chloride and sulfate attacks
429 from harsh seawater environments as well as salt crystallization is known to occur in concrete with
430 high cement contents [57]. The combined phenomena explain the deterioration of long-term
431 strength development of UHPC under seawater curing regime.

432 *[Figure 11 near here]*

433 Similar behavior has been observed in SCM-based UHP-SWSSC. In comparison with seawater
434 curing, 50% OPC replaced UHP-SWSSC mixes attain a compressive strength increase of 18.5%,
435 9.6%, 10%, and 9.7% respectively after the age of 3, 7, 28, and 90 days in tap water curing
436 **(Figure 12)**. Contrary to OPC-based UHPC, early age strength is more impacted than long-term
437 strength in slag and silica fume-based UHPC, regardless of the sand type utilized. The addition of
438 SCMs furthers the hydration reaction due to their enhanced pozzolanic activity, which continues
439 to densify the microstructure as time progresses. Therefore, SCM-based UHPC experiences lower
440 compressive strength loss under a harsh seawater environment [58].

441 *[Figure 12 near here]*

442 3.4. Shrinkage

443 3.4.1. Effect of sand type

444 **Figure 13** compares the total, autogenous, and drying shrinkage of UHPC comprising of three
445 different types of sand and that of conventional concrete. UHPCs experienced significantly higher
446 autogenous shrinkage, and therefore higher total shrinkage compared to normal concrete
447 (**Figure 13 (a, b)**). The 7 day early-age and 120 day long-term autogenous shrinkage of UHP-
448 SWSSC was found to be 15 and 6 times larger than that of normal concrete, respectively. As the
449 negligible water content in UHPC is not enough for complete hydration of binder contents, greater
450 surface tension is created in the fine capillary pores of the cementitious matrix, which leads to
451 larger autogenous shrinkage [23, 59]. UHPC experiences a very quick self-desiccation during the
452 first few days after casting and thus obtains a very high early autogenous strain rate. The early
453 growth (first 7 days) of autogenous shrinkage is slower in plain concrete. While normal concrete
454 reaches only 28% of its maximum autogenous shrinkage gained over 120 days testing period,
455 UHP-SWSSC reaches 72% of its maximum autogenous shrinkage in the same duration
456 (**Figure 14**). It can be observed from **Figure 15** that the proportion of autogenous shrinkage is
457 insignificant in NC (< 20% of total shrinkage) but it is significant in UHPC (over 40% in UHP-
458 SWSSC and over 60% in UHP-TWRSC as well as UHP-TWWBSC).

459 *[Figure 13 near here]*

460 UHPC manufactured from seawater and sea sand in this study yielded considerably higher drying
461 shrinkage strain than tap water and river sand or washed beach sand counterparts (**Figure 13(c)**),
462 whereas the autogenous shrinkages were quite similar (**Figure 13(b)**). After 120 days of testing
463 period, the drying shrinkage of UHP-SWSSC was 973.7 $\mu\epsilon$, compared to 288 $\mu\epsilon$ and 347.3 $\mu\epsilon$ for
464 UHP-TWWBSC and UHP-TWRSC respectively. Due to the presence of excessive sodium and

465 calcium chloride in seawater sea sand concrete, the morphology of the pore structure densifies,
466 which increased the number of micropores. This eventually increases the capillary tension and
467 therefore generates substantially high drying shrinkage [60, 61]. Additionally, the presence of sea-
468 shell contents may have accounted for larger drying shrinkage in sea sand-based concrete,
469 particularly due to the lower rigidity of sea-shell particles [62].

470 Although autogenous shrinkage dominates the total shrinkage in washed beach sand and river sand
471 UHPC mixes (with a ratio of 120 days autogenous to drying shrinkage to be 2.23 and 1.89,
472 respectively), the drying shrinkage strain component was observed to be larger in the seawater sea
473 sand variant (ratio of autogenous to drying shrinkage was 0.7). Over the whole testing timeframe,
474 autogenous shrinkage was less prominent in UHP-SWSSC (around 40-45% of the total shrinkage),
475 whereas it formulated the major portion of the total shrinkage in river sand and washed beach sand
476 UHPC (around 65-70%). It is evident from **Figure 14** that sea sand-based UHPC achieves 93% of
477 its maximum autogenous shrinkage after 28 days from casting, whereas washed beach sand and
478 river sand UHPCs reach respectively 75% and 73% at the same point of time. The increased
479 amount of calcium chloride as a result of reactions between sodium chloride and calcium
480 hydroxide in the pore solution of seawater-based UHPC is the prime reason behind its accelerated
481 hydration [63]. Autogenous shrinkage strain in UHP-SWSSC reaches a plateau after 21 days
482 indicating the completion of accelerated hydration, whereas it takes around 100 days to stabilize
483 in UHP-TWRSC and UHP-TWWBSC. Therefore, UHP-SWSSC may be susceptible to early-age
484 cracking due to its high early-age autogenous shrinkage.

485 *[Figure 14 near here]*

486 Overall, the growth of drying shrinkage in UHP-SWSSC is slower than river sand and washed
487 beach sand UHPCs. Drying shrinkage strain in UHP-SWSSC stabilizes after 84 days of casting,
488 while UHP-TWRSC and UHP-TWWBSC take only around 21 days to attain plateau. Very small
489 pores in the compact microstructure of UHP-SWSSC continue their capillary actions for an
490 extended time, which leads to the gradual increase of the drying shrinkage.

491 *[Figure 15 near here]*

492 3.4.2. *Effect of SCMs*

493 It was observed from **Figure 16(a)** that replacement of OPC by SCMs tends to decrease the overall
494 shrinkage of seawater and sea sand-based UHPC. Although the autogenous shrinkage was found
495 to moderately increase (**Figure 16(b)**), the drying shrinkage considerably reduced when OPC was
496 partially replaced by slag and silica fume (**Figure 16(c)**).

497 *[Figure 16 near here]*

498 A more detailed comparison on the growth of autogenous shrinkage suggests that the autogenous
499 shrinkage in OPC-slag-silica fume ternary mix was lower than OPC-slag binary mix. However,
500 both types of mixes yielded greater autogenous shrinkage compared to cement-only UHPC.
501 Incorporation of slag and silica fume is known to enhance the autogenous shrinkage of concrete
502 due to their ability to refine the microstructure into a finer pore capillary system, which increases
503 the degree of self-desiccation, leading to a higher autogenous shrinkage [64, 65]. Generally, the
504 effect of silica fume in hydration is much more pronounced in fresh water-based UHPC compared
505 to that of slag, especially at early ages. However, due to the alkaline environment and presence of
506 a high quantity of sulfates in the pore solution of seawater mixed UHPC matrix, the hydration
507 reaction of slag accelerates and the reactivity of silica fume with cement reduces [63]. The rapid

508 dissolution of slag and decelerated influence of silica fume in the hydration kinetics of UHP-
509 SWSSC explains the larger autogenous shrinkage of OPC-slag UHPC compared to OPC-slag-
510 silica fume ternary blends. However, as the slag content in ternary mixes increased, the autogenous
511 shrinkage values also increased. After 120 days, the binary (25% OPC substitution by only slag)
512 and ternary (37.5% OPC replacement by 25% slag and 12.5% silica fume) mixes yielded 50.9%
513 and 6.7% higher autogenous shrinkage, respectively compared to the control mix. Blast furnace
514 slag in UHP-SWSSC significantly elevates autogenous shrinkage, while further addition of silica
515 fume balances this surge. **Figure 17** demonstrates the SEM images of shrinkage cracks in the
516 microstructure of control UHP-SWSSC (**Figure 17(a)**) and the blend with 25% OPC replaced by
517 slag (**Figure 17(b)**). As the samples right after casting were sealed in closed plastic tubes and
518 remained sealed until the day of SEM analysis, the shrinkage that occurred in the specimens was
519 primarily autogenous shrinkage. A prominent network of autogenous shrinkage cracks was seen
520 in the microstructure of 25% OPC replaced UHPC compared to UHPC with 100% OPC, where
521 autogenous shrinkage cracks were almost nonexistent.

522 *[Figure 17 near here]*

523 The inclusion of slag and silica fume accelerates the growth of autogenous shrinkage development
524 as well. This is from the higher degree of reaction of cement from the addition of SCMs as captured
525 in the heat evolved per gram of cement (shown in **Figure 4**). In the control mix, drying shrinkage
526 grows more rapidly than autogenous shrinkage (88% of drying and 50% of autogenous shrinkage
527 develops in the first 7 days, as demonstrated in **Figure 18**). However, with more portion of OPC
528 being replaced by slag and silica fume, autogenous shrinkage starts to grow quicker at early ages
529 due to elevated interaction of slag in the cement-slag-silica fume ternary blends. For a 50%, OPC

530 replaced mix, 72% autogenous shrinkage develops after 7 days as opposed to 68% drying
531 shrinkage.

532 *[Figure 18 near here]*

533 In general, the percentage of autogenous shrinkage with respect to total shrinkage increases with
534 an increase in OPC replacement percentage. This applies especially to the OPC-slag binary mix,
535 where autogenous shrinkage was 53% of the total shrinkage at 120 days, compared to 33% in the
536 control mix (**Figure 19**). OPC replaced by only slag (or high content of slag) produces a high value
537 of autogenous to drying shrinkage ratio. For instance, a 25% substitution of OPC by slag yielded
538 an autogenous to drying shrinkage ratio of 1.14, compared to 0.49 for the control mix. Autogenous
539 shrinkage was most significant in SS-62.5-0.2 (50% slag and 12.5% silica fume) as a result of its
540 high slag inclusion (autogenous to drying shrinkage ratio of 1.28).

541 Drying shrinkage decrease with the increase of cement substitution by slag and silica fume unlike
542 autogenous shrinkage, which is consistent with relevant literature [66]. This is attributed to the
543 relatively denser microstructure in slag-based UHPC. A compact matrix contains lesser
544 microstructural pores, which keeps water loss due to evaporation to a minimum and therefore leads
545 to a decreased drying shrinkage. It was also noticed that drying shrinkage in silica fume added
546 mixes grew slower than control and OPC-slag binary mixes. After 7 days of casting, the SS-62.5-
547 0.2 ternary mix develops 72% of its ultimate drying shrinkage, compared to 88% and 94% growth
548 in control and 25% slag replaced mixes, respectively (**Figure 18**). This delayed growth of drying
549 shrinkage is probably because silica fume further densifies OPC-slag binary system and yields a
550 more compact microstructure. In general, drying shrinkage becomes less prominent with more
551 percentage of OPC supplanted by slag and silica fume.

552 *[Figure 19 near here]*

553 *3.4.3. Effect of water-to-binder ratio*

554 **Figure 20** illustrates the effect of the water-to-binder ratio on the shrinkage of UHP-SWSSC. From
555 **Figure 20(c)**, it is observed that the drying shrinkage in the UHPC with higher water content is
556 larger than the lower water-to-binder ratio counterparts (701.6 $\mu\epsilon$ in SS-0.50-0.15 compared to
557 1090 $\mu\epsilon$ in SS-50-0.25 after 120 days of casting). More pores are formed in a concrete mix with
558 larger water content, which produces higher surface tension in the pore structure during
559 evaporation [26].

560 *[Figure 20 near here]*

561 Several literatures have reported an increase in autogenous shrinkage with the reduction of water-
562 to-cement ratio in high-performance concrete [59], ultra-high performance concrete [64], and
563 reactive powder concrete [26] as a result of enhanced internal drying, self-desiccation, and
564 capillary tension. However, a quite opposite finding has been obtained in this research regarding
565 seawater and sea sand-based UHPCs. From **Figure 20 (b)**, the autogenous shrinkage was observed
566 to increase with the increase in the water-to-binder ratio of UHP-SWSSC. Autogenous shrinkage
567 grew faster when the water-to-binder ratio was higher, especially at early ages, which may have
568 occurred due to the effect of seawater on the ternary blend of OPC, slag, and silica fume. For
569 example, 69% and 80% of maximum autogenous shrinkage were reached in the first 7 days for
570 mixes with the water-to-binder ratio of 0.15 and 0.25, respectively (**Figure 21**). As discussed in
571 **Section 3.4.2**, the incorporation of seawater in pastes with a low water-to-binder ratio can increase
572 the reactivity of slag, especially at early ages [63]. A higher amount of seawater-induced ions and
573 higher alkalinity in mixes with larger water content can accelerate the hydration rate of slag to a

574 greater extent, which means enhanced self-desiccation and greater autogenous shrinkage. This
575 mechanism also explains the rapid initiation of autogenous shrinkage in higher water-to-binder
576 ratio mixes. It is evident from **Figure 21** that the development of autogenous shrinkage is lower
577 than drying shrinkage during the first 7 days in the SS-50-0.15 mix. However, for SS-50-0.25 mix
578 with higher water content, growth of autogenous shrinkage after 7 and 28 days was significantly
579 higher than drying shrinkage. No clear trend regarding the proportions of autogenous and drying
580 shrinkage was obtained in mixes with different water-to-binder ratios (**Figure 22**).

581 *[Figure 21 near here]*

582 Although autogenous shrinkage usually governs the overall shrinkage in reactive powder concrete,
583 overall drying shrinkage was found to be dominant in seawater and sea sand-based UHPC in this
584 study, with a couple of exceptions of OPC-slag binary mix (SS-25-0.2) and a large portion of slag
585 incorporated ternary mix (SS-62.5-0.2). The relatively lower proportion of autogenous shrinkage
586 in UHP-SWSSC is advantageous particularly in terms of early-age autogenous shrinkage-induced
587 cracking.

588 *[Figure 22 near here]*

589 **4. Selection of a Proper Mix based on Physical, Mechanical and Dimensional Stability** 590 **Properties**

591 Physical, mechanical, and dimensional stability properties of the industrial by-product based
592 seawater and sea sand UHPC mixes are compared in **Table 8** to evaluate their performance.
593 Properties of the individual mixes were compared against the control mix (SS-0-0.2). An increase
594 or a decrease in the properties with respect to the control mix has been quantified by a positive or
595 negative percentage, respectively. It is evident from the comparison that the OPC replaced UHP-

596 SWSSC mixes possessed slightly lower fresh as well as 28-day unit weight. Workability of UHP-
597 SWSSC can be an issue if a high proportion of slag is added (>37.5% of the total binder) or the
598 water-to-binder ratio is kept relatively low (<0.2). Although early age compressive strengths were
599 smaller than the control mix, strength increased with time and exceeded the control mix after 90
600 days. Overall, autogenous shrinkage was higher (except SS-50-0.15) and drying shrinkage was
601 lower with respect to the control mix. When added together, total shrinkage was also lower
602 compared to the control mix (except SS-50-0.25). Comparing the mechanical and dimensional
603 stability properties, the SS-50-0.2 mix is recommended in this study. Compared to the control mix,
604 this mix achieved slightly higher long-term strength (7.47%) and lower total shrinkage strain
605 (10.95%) without compromising the workability. Although a marginal reduction in workability
606 (5.56%) and a moderate increase in the autogenous shrinkage (15.92%) was observed, this blend
607 yielded satisfactory performance among other UHP-SWSSC mixes with different OPC
608 substitution percentages and water-to-binder ratios.

609 XRF analysis of ground concrete powder reveals the chloride content of mature UHPC samples.
610 Most importantly, the chloride content of the seawater and sea sand UHPC mix was determined to
611 be 8.0 kg/m^3 , as opposed to 0.72 kg/m^3 for tap water and river sand-based UHPC. Chloride content
612 found in UHP-SWSSC was found to be 10 times higher than the AS 1379 [67] limits of 0.8 kg/m^3
613 for normal class concrete. However, the experimental results of this study provide evidence that
614 marine resources can still be utilized in UHPC fabrication for unreinforced applications or may be
615 embedded with corrosion-resistant reinforcement, such as FRPs. The durability study of seawater
616 and sea sand UHPC mixes which is currently underway by this research group will provide critical
617 data for a well-informed cost-benefit-sustainability analysis.

618 *[Table 8 near here]*

619 **5. Conclusions**

620 The following conclusions can be drawn within the limited scope of this preliminary study on the
621 potential of using seawater and sea sand in UHPC fabrication:

- 622 • Seawater accelerates cement hydration and releases more heat from the formation of Friedel's
623 salt in the early ages of hydration. This is also reflected in the early-age compressive strength.
- 624 • Incorporation of seawater and sea sand in UHPC yields marginally higher fresh and hardened
625 density compared to river sand and washed beach sand counterparts, whereas industrial by-
626 products such as ground slag and silica fume reduce the unit weight of UHP-SWSSC.
- 627 • The use of sea sand and seawater in UHPC slightly decreases its workability. However, silica
628 fume in an OPC-slag-silica fume ternary blend offers better workability compared to OPC-
629 slag binary blends. A sufficiently workable mix at a water-to-binder ratio of 0.2 can be
630 achieved under an optimized superplasticizer dose with a maximum 50% OPC replacement
631 with SCMs.
- 632 • Sea sand and seawater UHPCs provide a higher rate of strength development especially up to
633 28 days, beyond which, the strength development slows down to reach similar 90 days
634 strength. Slag and silica fume offer a similar 90 days strength from the delayed secondary
635 hydration products from their pozzolanic reactivity. The optimum water-to-binder ratio to
636 achieve maximum long-term compressive strength was found to be 0.2.
- 637 • Seawater curing lowers the long-term strength of OPC-based UHPC and the early age strength
638 of SCM incorporated UHPC. However, UHPC with SCMs experiences marginal deterioration
639 under seawater environment compared to cement-only counterpart.
- 640 • UHP-SWSSC produces high early-age autogenous shrinkage and considerably higher drying
641 shrinkage than tap water and river sand or washed beach sand variants because of the

642 accelerated hydration of cement. SCM incorporation in the mix also increases autogenous
643 shrinkage from the accelerated hydration of cement particles, but significantly reduces drying
644 shrinkage from densifying the UHPC matrix, and hence reduces the overall shrinkage.

- 645 • A UHP-SWSSC mix with 50% OPC replaced by 37.5% slag and 12.5% silica fume is
646 recommended in this study, which can achieve satisfactory workability, long-term strength,
647 and dimensional stability properties.

648 **Acknowledgments**

649 This study has been funded by the Australian Research Council (ARC) through an ARC Discovery
650 Grant (DP160100739). The authors wish to acknowledge Randwick Council for their permission
651 to collect seawater and sea sand from Malabar beach in Sydney, NSW. We thank Mr. William
652 Terry and Mr. Luiz Pettersen, technical staff of the Infrastructure Laboratory at UNSW for their
653 assistance in the preparation of specimens. Finally, the authors also acknowledge the use of
654 facilities within the Mark Wainwright Analytical Centre at UNSW for X-ray fluorescence
655 spectroscopy and scanning electron microscopy.

656 **References**

- 657 1. <https://www.statista.com/statistics/1087115/global-cement-production-volume/> (accessed
658 on 08.12.2021).
- 659 2. Xiao J, Qiang C, Nanni A, et al., Use of sea-sand and seawater in concrete construction:
660 Current status and future opportunities. *Construction and Building Materials*, 2017. **155**:
661 p. 1101-1111.
- 662 3. Ercikdi B, Cihangir F, Kesimal A, et al., Utilization of industrial waste products as
663 pozzolanic material in cemented paste backfill of high sulphide mill tailings. *Journal of*
664 *Hazardous Materials*, 2009. **168**(2): p. 848-856.

- 665 4. Kumar R, Samanta AK and Roy DKS, Characterization and development of eco-friendly
666 concrete using industrial waste - a review. *Journal of Urban and Environmental*
667 *Engineering*, 2014. **8**(1): p. 98-108.
- 668 5. Teng J, Yu T, Dai J, et al. *FRP composites in new construction: current status and*
669 *opportunities*. in *Proceedings of 7th National Conference on FRP Composites in*
670 *Infrastructure (Supplementary Issue of Industrial Construction)*, keynote presentation,
671 *Hangzhou, China*. 2011.
- 672 6. Li YL, Zhao XL, Singh RKR, et al., Experimental study on seawater and sea sand concrete
673 filled GFRP and stainless steel tubular stub columns. *Thin-Walled Structures*, 2016. **106**:
674 p. 390-406.
- 675 7. Wang Z, Zhao X-L, Xian G, et al., Long-term durability of basalt- and glass-fibre
676 reinforced polymer (BFRP/GFRP) bars in seawater and sea sand concrete environment.
677 *Construction and Building Materials*, 2017. **139**: p. 467-489.
- 678 8. Dong Z-Q, Wu G, Zhao X-L, et al., Long-Term Bond Durability of Fiber-Reinforced
679 Polymer Bars Embedded in Seawater Sea-Sand Concrete under Ocean Environments.
680 2018. **22**(5): p. 04018042.
- 681 9. Zeng J-J, Gao W-Y, Duan Z-J, et al., Axial compressive behavior of polyethylene
682 terephthalate/carbon FRP-confined seawater sea-sand concrete in circular columns.
683 *Construction and Building Materials*, 2020. **234**: p. 117383.
- 684 10. Ramaswamy S, Aziz M and Murthy C, *Sea dredged sand for concrete*, in *Extending*
685 *Aggregate Resources*. 1982, ASTM International.
- 686 11. Kaushik SK and Islam S, Suitability of sea water for mixing structural concrete exposed to
687 a marine environment. *Cement and Concrete Composites*, 1995. **17**(3): p. 177-185.
- 688 12. Mohammed TU, Hamada H and Yamaji T, Performance of seawater-mixed concrete in the
689 tidal environment. *Cement and Concrete Research*, 2004. **34**(4): p. 593-601.
- 690 13. Etxeberria M, Fernandez JM and Limeira J, Secondary aggregates and seawater
691 employment for sustainable concrete dyke blocks production: Case study. *Construction*
692 *and Building Materials*, 2016. **113**: p. 586-595.
- 693 14. Islam MM, Islam MS, Al-Amin M, et al., Suitability of sea water on curing and
694 compressive strength of structural concrete. *Journal of Civil Engineering (IEB)*, 2012.
695 **40**(1): p. 37-45.

- 696 15. Cui M, Mao J-Z, Jia D-G, et al. *Experimental study on mechanical properties of marine*
697 *sand and seawater concrete*. in *Proceedings of the 2014 International Conference on*
698 *Mechanics and Civil Engineering*. 2014.
- 699 16. Limeira J, Agulló L and Etxeberria M, Dredged marine sand as a new source for
700 construction materials. *Materiales de Construcción*, 2012. **62**(305): p. 7-24.
- 701 17. Modupeola AG and Olutoge FA, The effect of seawater on shrinkage properties of
702 concrete. *Int J Res Eng Technol*, 2014. **2**(10): p. 1-12.
- 703 18. Younis A, Ebead U, Suraneni P, et al. *Strength, shrinkage, and permeability performance*
704 *of seawater concrete*. in *10th International Structural Engineering and Construction*
705 *Conference, ISEC 2019*. 2019. ISEC Press.
- 706 19. Mahanama D, Silva PD, Kim T, et al., Evaluating Effect of GGBFS in Alkali Silica
707 Reaction in Geopolymer Mortar with Accelerated Mortar Bar Test. *ASCE Journal of*
708 *Materials in Civil Engineering*, 2019. **31**(8): p. 04019167.
- 709 20. Balázs GLE, *Structural concrete: textbook on behaviour, design and performance. 1*. 2009:
710 International Federation for Structural Concrete.
- 711 21. ASTM C1856 / C1856M-17 Standard practice for fabricating and testing specimens of
712 ultra-high performance concrete. 2017, ASTM International: West Conshohocken.
- 713 22. Shi C, Wu Z, Xiao J, et al., A review on ultra high performance concrete: Part I. Raw
714 materials and mixture design. *Construction and Building Materials*, 2015. **101**: p. 741-751.
- 715 23. Mishra O and Singh SP, An overview of microstructural and material properties of ultra-
716 high-performance concrete. *Journal of Sustainable Cement-Based Materials*, 2019. **8**(2):
717 p. 97-143.
- 718 24. Wang D, Shi C, Wu Z, et al., A review on ultra high performance concrete: Part II.
719 Hydration, microstructure and properties. *Construction and Building Materials*, 2015. **96**:
720 p. 368-377.
- 721 25. Schröfl C, Gruber M and Plank J, Preferential adsorption of polycarboxylate
722 superplasticizers on cement and silica fume in ultra-high performance concrete (UHPC).
723 *Cement and Concrete Research*, 2012. **42**(11): p. 1401-1408.
- 724 26. Tam CM, Tam VWY and Ng KM, Assessing drying shrinkage and water permeability of
725 reactive powder concrete produced in Hong Kong. *Construction and Building Materials*,
726 2012. **26**(1): p. 79-89.

- 727 27. Xie T, Fang C, Mohamad Ali MS, et al., Characterizations of autogenous and drying
728 shrinkage of ultra-high performance concrete (UHPC): An experimental study. *Cement*
729 *and Concrete Composites*, 2018. **91**: p. 156-173.
- 730 28. Han J, Fang H and Wang K, Design and control shrinkage behavior of high-strength self-
731 consolidating concrete using shrinkage-reducing admixture and super-absorbent polymer.
732 *Journal of Sustainable Cement-Based Materials*, 2014. **3**(3-4): p. 182-190.
- 733 29. Teng J-G, Xiang Y, Yu T, et al., Development and mechanical behaviour of ultra-high-
734 performance seawater sea-sand concrete. 2019. **22**(14): p. 3100-3120.
- 735 30. AS 3972 General purpose and blended cements. 2010, Standards-Australia.
- 736 31. AS 3582.2 Supplementary cementitious materials for use with portland and blended
737 cement Slag - Ground granulated iron blast-furnace. 2016, Standards Australia.
- 738 32. AS/NZS 3582.3-2002 Supplementary cementitious materials for use with portland and
739 blended cement - Amorphous silica. 2002, Standards-Australia.
- 740 33. Wille K and Boisvert-Cotulio C, Material efficiency in the design of ultra-high
741 performance concrete. *Construction and Building Materials*, 2015. **86**: p. 33-43.
- 742 34. AS 1141.11.1 Methods for sampling and testing aggregates Particle size distribution -
743 Sieving method. 2009, Standards Australia.
- 744 35. AS 1141.5 Methods for sampling and testing aggregates—particle density and water
745 absorption of fine aggregate. 2000, Standards-Australia.
- 746 36. AS 1141.4-2000 Methods for sampling and testing aggregates, Method 4: Bulk density of
747 aggregate. 2000, Standards-Australia.
- 748 37. ASTM C29 / C29M - 17a Standard Test Method for Bulk Density (“Unit Weight”) and
749 Voids in Aggregate. 2017, ASTM International: West Conshohocken, PA.
- 750 38. AS 1478.1-2000 Chemical admixtures for concrete, mortar and grout Admixtures for
751 concrete. 2000, Standards-Australia.
- 752 39. ASTM C1437-15, Standard Test Method for Flow of Hydraulic Cement Mortar. 2015,
753 ASTM International: West Conshohocken, PA.
- 754 40. ASTM C138 Standard Test Method for Density (Unit Weight), Yield, and Air Content
755 (Gravimetric) of Concrete. 2017, ASTM International: West Conshohocken, PA.

- 756 41. ASTM C109 / C109M - 21 Standard Test Method for Compressive Strength of Hydraulic
757 Cement Mortars (Using 2-in. or [50 mm] Cube Specimens). 2021, ASTM International:
758 West Conshohocken.
- 759 42. AS 1012.13 Methods of testing concrete Determination of the drying shrinkage of concrete
760 for samples prepared in the field or in the laboratory. 2015, Standards Australia.
- 761 43. Gartner E, Young J, Damidot D, et al., *Hydration of Portland cement*, in *Structure and*
762 *Performance of Cements*. 2002, CRC Press. p. 57-108.
- 763 44. Farnam Y, Dick S, Wiese A, et al., The influence of calcium chloride deicing salt on phase
764 changes and damage development in cementitious materials. *Cement and Concrete*
765 *Composites*, 2015. **64**: p. 1-15.
- 766 45. Li P, Li W, Yu T, et al., Investigation on early-age hydration, mechanical properties and
767 microstructure of seawater sea sand cement mortar. *Construction and Building Materials*,
768 2020. **249**: p. 118776.
- 769 46. Lothenbach B, Scrivener K and Hooton R, Supplementary cementitious materials. *Cement*
770 *and Concrete Research*, 2011. **41**(12): p. 1244-1256.
- 771 47. Hjorth J, Skibsted J and Jakobsen HJ, ²⁹Si MAS NMR studies of portland cement
772 components and effects of microsilica on the hydration reaction. *Cement and Concrete*
773 *Research*, 1988. **18**(5): p. 789-798.
- 774 48. Zain MFM, Safiuddin M and Yusof KM, A study on the properties of freshly mixed high
775 performance concrete. *Cement and Concrete Research*, 1999. **29**(9): p. 1427-1432.
- 776 49. Turk K, Viscosity and hardened properties of self-compacting mortars with binary and
777 ternary cementitious blends of fly ash and silica fume. *Construction and Building*
778 *Materials*, 2012. **37**: p. 326-334.
- 779 50. Eide MB and Hisdal J-M, Ultra High Performance Fibre Reinforced Concrete (UHPFRC)–
780 State of the art; 2012. (Coin Project Report–44).
- 781 51. Zhang J and Zhao Y, The mechanical properties and microstructure of ultra-high-
782 performance concrete containing various supplementary cementitious materials. *Journal*
783 *of Sustainable Cement-Based Materials*, 2017. **6**(4): p. 254-266.
- 784 52. Van Tuan N, Ye G, van Breugel K, et al., The study of using rice husk ash to produce ultra
785 high performance concrete. *Construction and Building Materials*, 2011. **25**(4): p. 2030-
786 2035.

- 787 53. Chen Y, Matalkah F, Soroushian P, et al., Optimization of ultra-high performance concrete,
788 quantification of characteristic features. *Cogent Engineering*, 2019. **6**(1): p. 1558696.
- 789 54. Sakir S, Raman SN, Safiuddin M, et al., Utilization of By-Products and Wastes as
790 Supplementary Cementitious Materials in Structural Mortar for Sustainable Construction.
791 2020. **12**(9): p. 3888.
- 792 55. Du H, Du S and Liu X, Durability performances of concrete with nano-silica. *Construction
793 and Building Materials*, 2014. **73**: p. 705-712.
- 794 56. Zhang X and Zhang H, Experimental Research on Ultra-High Performance Concrete
795 (UHPC). *IOP Conference Series: Materials Science and Engineering*, 2019. **562**(1): p.
796 012045.
- 797 57. Kuhail Z and Shihada S, Effect of Gaza seawater on concrete strength for different
798 exposures. *IUG Journal for Natural Engineering Studies*, 2003. **11**(2).
- 799 58. Binici H, Aksogan O, Görür EB, et al., Performance of ground blast furnace slag and
800 ground basaltic pumice concrete against seawater attack. *Construction and Building
801 Materials*, 2008. **22**(7): p. 1515-1526.
- 802 59. Wu L, Farzadnia N, Shi C, et al., Autogenous shrinkage of high performance concrete: A
803 review. *Construction and Building Materials*, 2017. **149**: p. 62-75.
- 804 60. Park SS, Kwon S-J and Song H-W, Analysis technique for restrained shrinkage of concrete
805 containing chlorides. *Materials and Structures*, 2011. **44**(2): p. 475-486.
- 806 61. Dhondy T, Xiang Y, Yu T, et al., Effects of mixing water salinity on the properties of
807 concrete. 2021. **24**(6): p. 1150-1160.
- 808 62. Yang E-I, Kim M-Y, Park H-G, et al., Effect of partial replacement of sand with dry oyster
809 shell on the long-term performance of concrete. *Construction and Building Materials*,
810 2010. **24**(5): p. 758-765.
- 811 63. Li H, Farzadnia N and Shi C, The role of seawater in interaction of slag and silica fume
812 with cement in low water-to-binder ratio pastes at the early age of hydration. *Construction
813 and Building Materials*, 2018. **185**: p. 508-518.
- 814 64. Liu J, Shi C and Wu Z, Hardening, microstructure, and shrinkage development of UHPC:
815 A review. *Journal of Asian Concrete Federation*, 2019. **5**(2): p. 1-19.
- 816 65. Lee KM, Lee HK, Lee SH, et al., Autogenous shrinkage of concrete containing granulated
817 blast-furnace slag. *Cement and Concrete Research*, 2006. **36**(7): p. 1279-1285.

818 66. Hale WM, Freyne SF, Bush TD, et al., Properties of concrete mixtures containing slag
819 cement and fly ash for use in transportation structures. *Construction and Building*
820 *Materials*, 2008. **22**(9): p. 1990-2000.

821 67. AS 1379 Specification and supply of concrete. 2007, Standards Australia.

822



(a)



(b)

Figure 1. Preparation and modification of sea sand (a) Impurities in sea sand, (b) sea sand after processing.



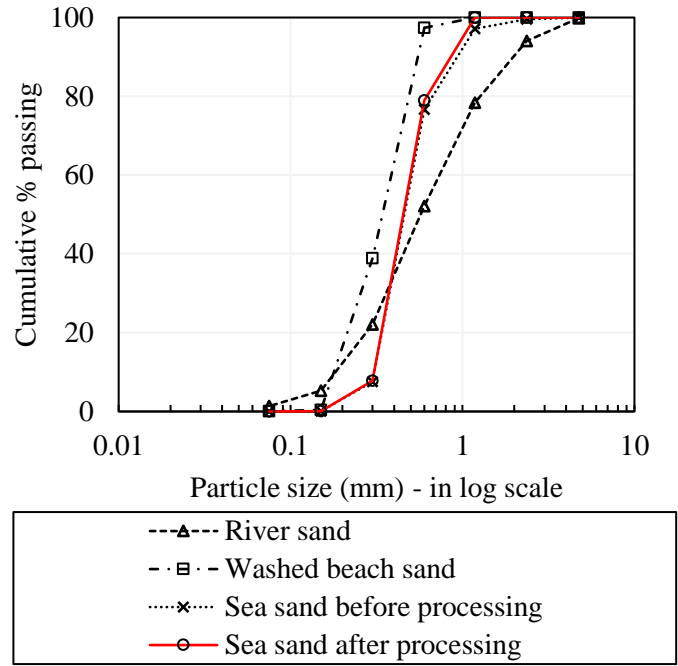



Figure 2. Particle size distribution curves of different sand aggregates (cumulative passing).

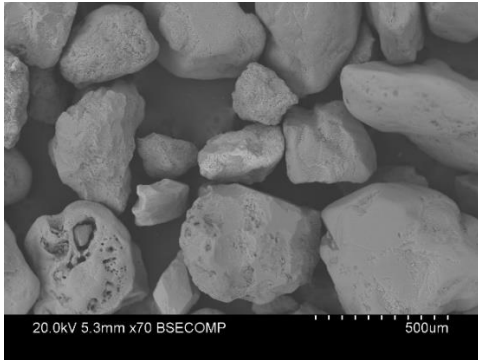


(a)

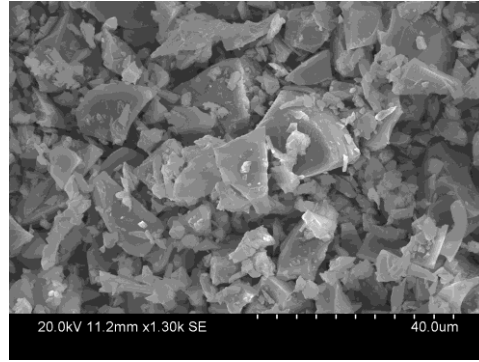


(d)

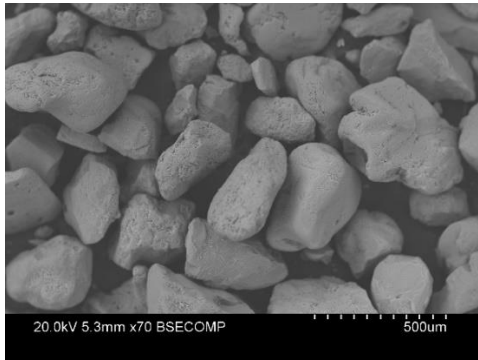

(b)

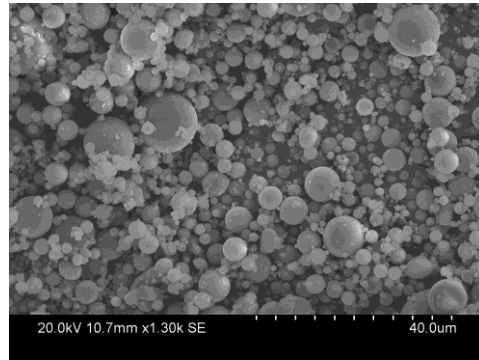

(e)

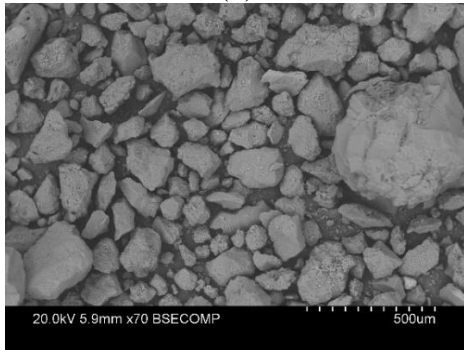

(c)

Figure 3. SEM images of different sand particles and SCMs (a) Sea sand, (b) washed beach sand, (c) river sand, (d) ground slag, (e) silica fume.

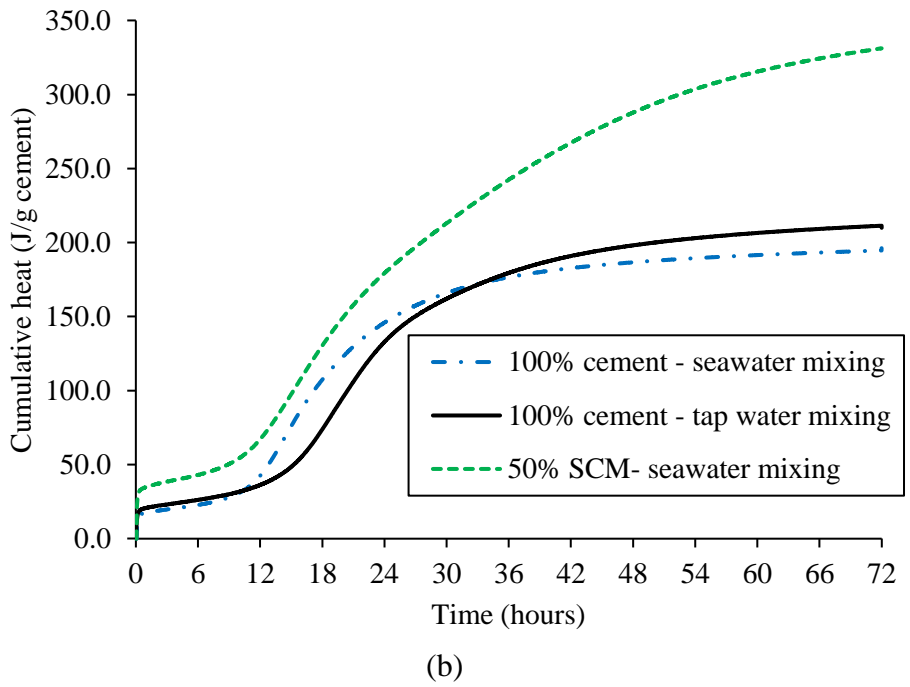
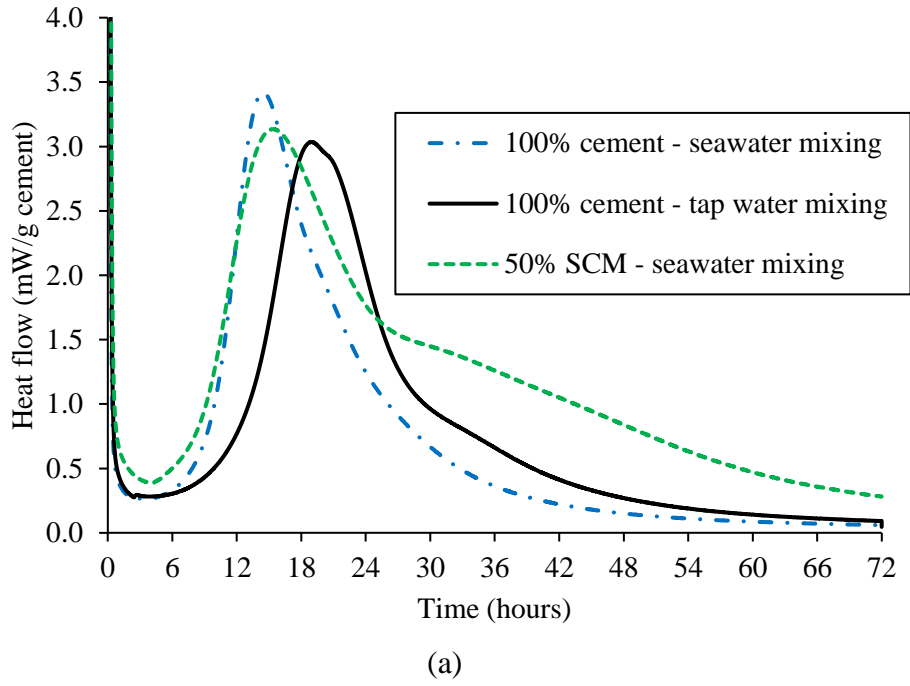


Figure 4. (a) Heat flow and (b) cumulative heat captured in an isothermal condition in the first 72 hours of hydration.

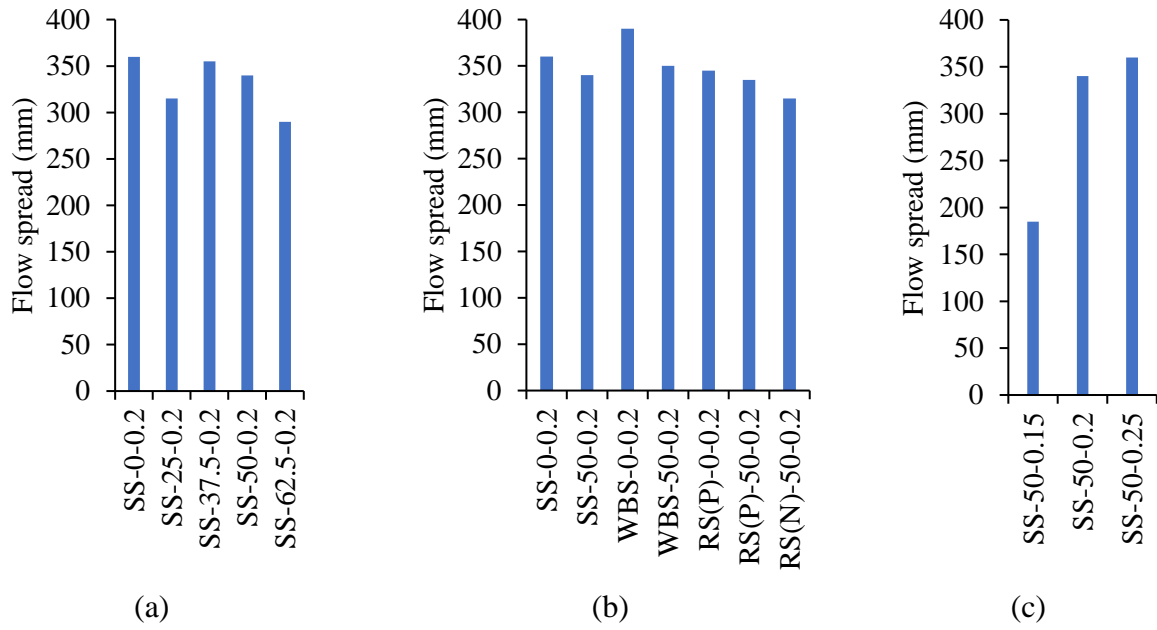


Figure 5. Comparison of workability of fresh UHP-SWSSC (by flow table test) based on (a) percentage of OPC replacement, (b) water to binder ratio, (c) different sand types.

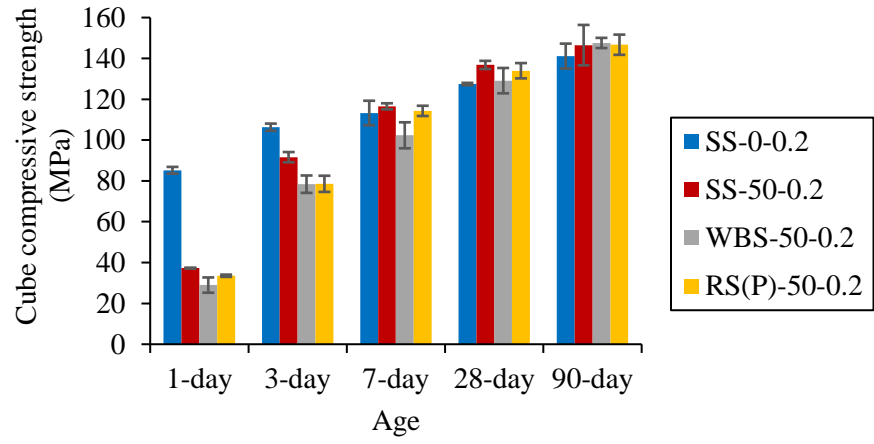


Figure 6. Effect of seawater and sea sand as mixing water and aggregate (tap water curing).

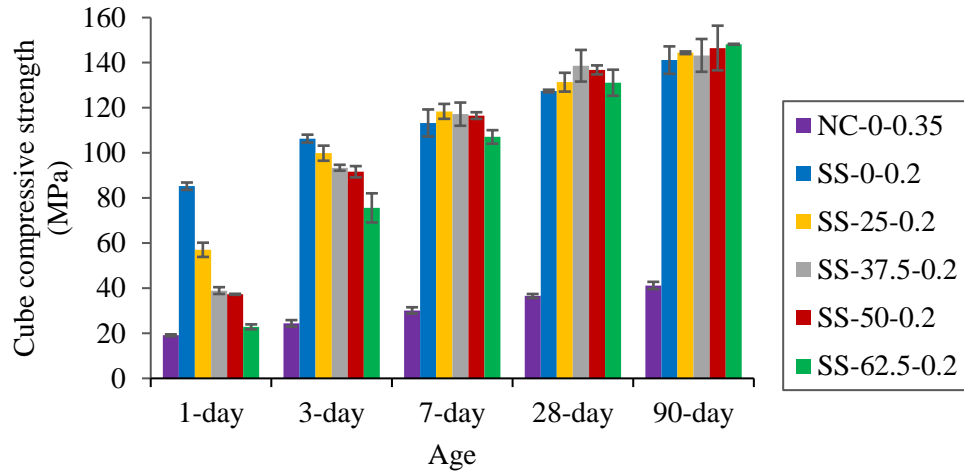


Figure 7. Effect of OPC replacement on cube compressive strength of UHP-SWSSC (tap water curing).

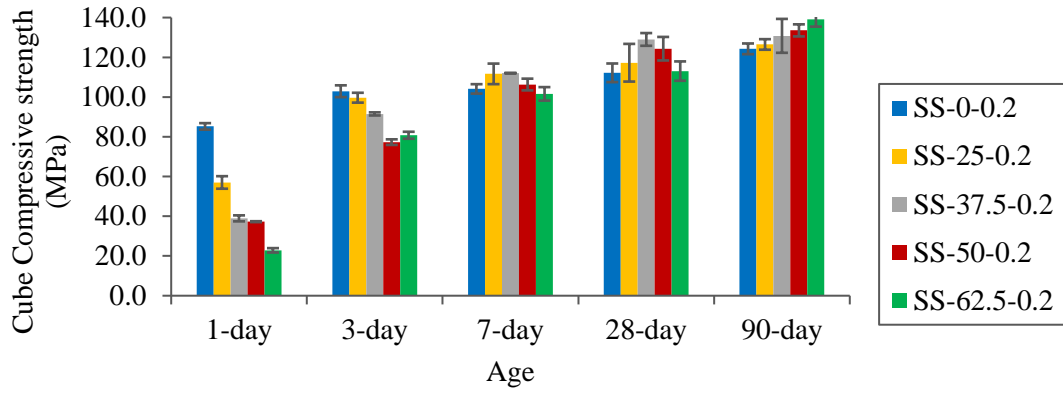


Figure 8. Effect of OPC replacement on cube compressive strength of UHP-SWSSC (seawater curing).

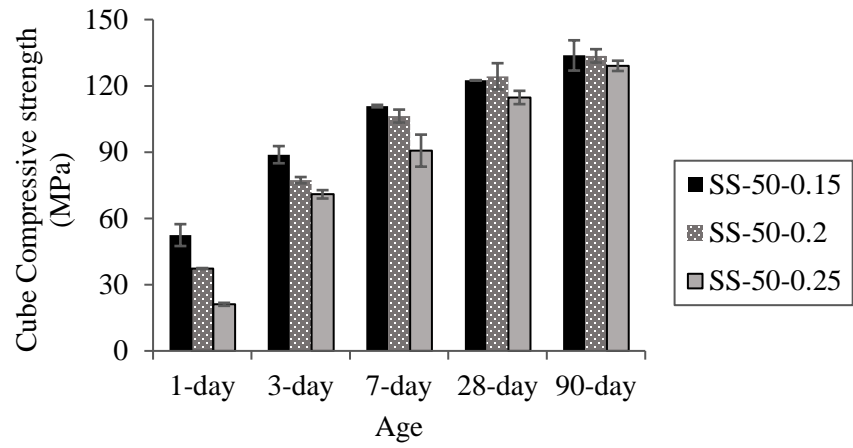


Figure 9. Effect of water to binder ratio on cube compressive strength (seawater curing).

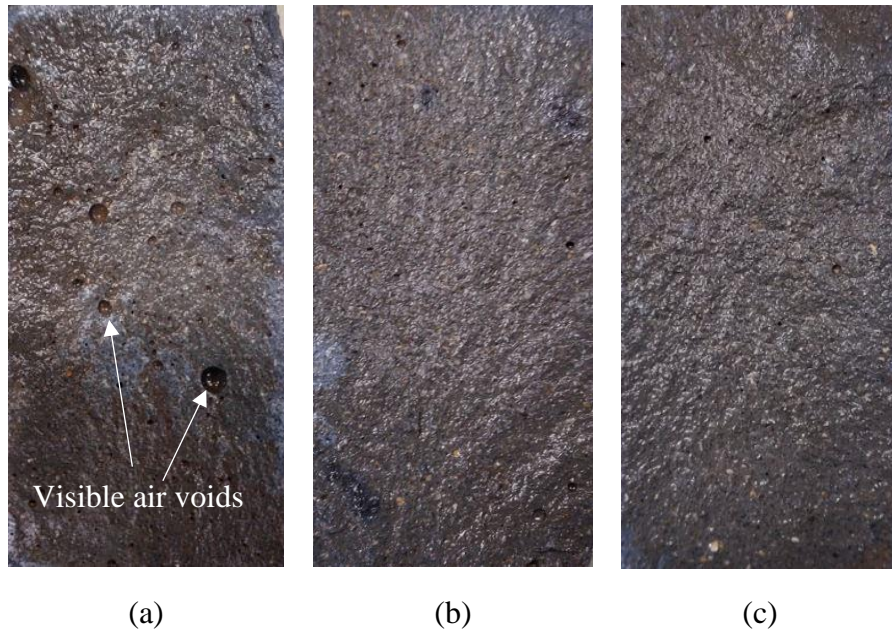


Figure 10. Cross-sections of UHP-SWSSC with different water to binder ratio (a) SS-50-0.15, (b) SS-50-0.2, (c) SS-50-0.25.

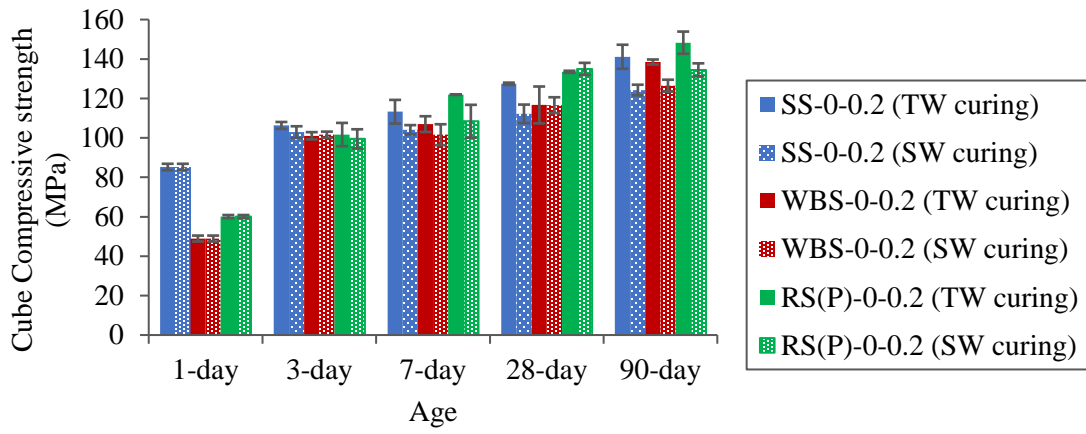


Figure 11. Effect of seawater curing on UHPC (100% OPC) with different aggregate types.



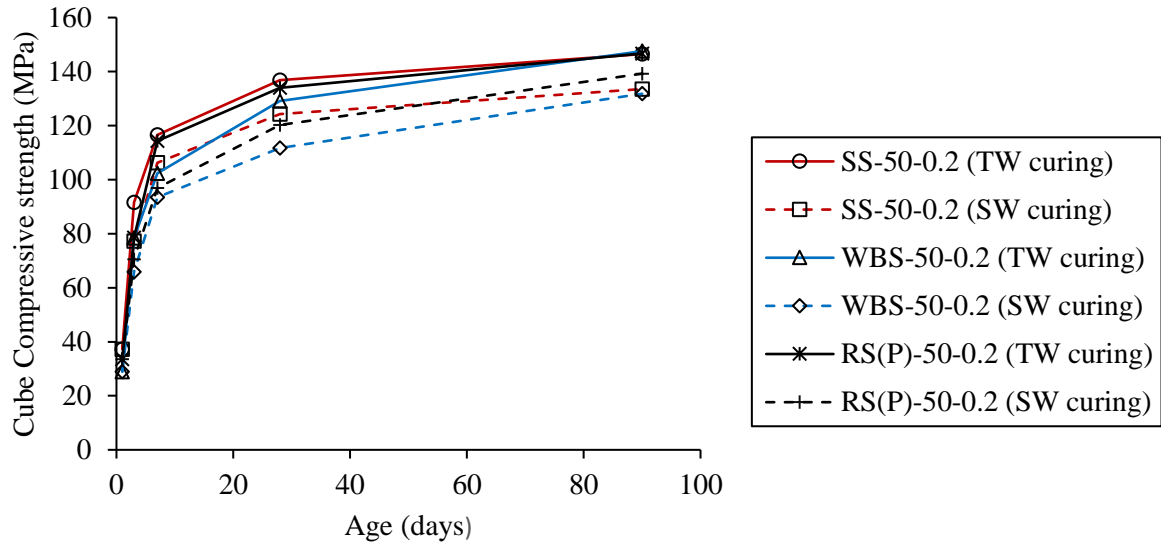



Figure 12. Effect of seawater curing on UHPC (50% OPC replacement) with different aggregate types.

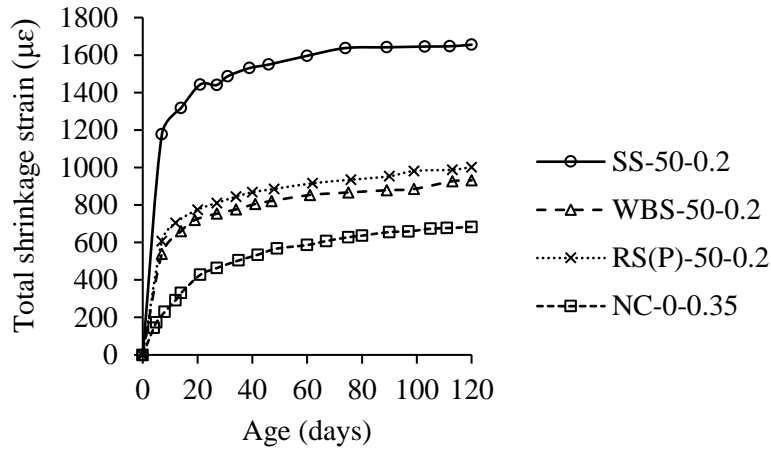

(a)

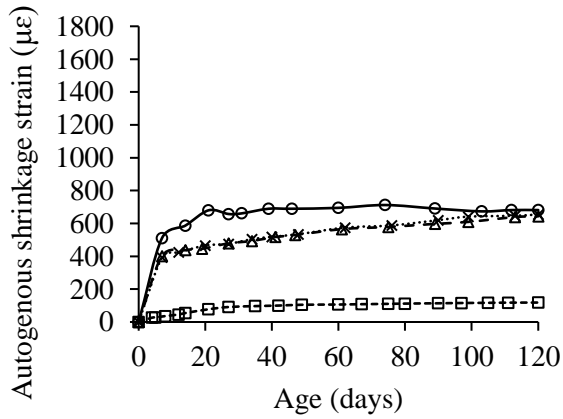


(b)

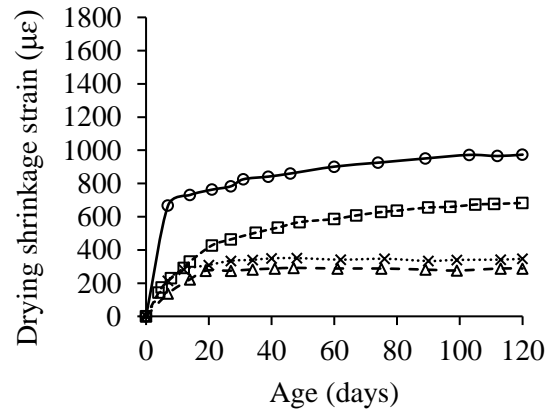

(c)

Figure 13. Effect of sand types on shrinkage of UHPC (a) Total shrinkage, (b) Autogenous shrinkage, (c) Drying shrinkage.

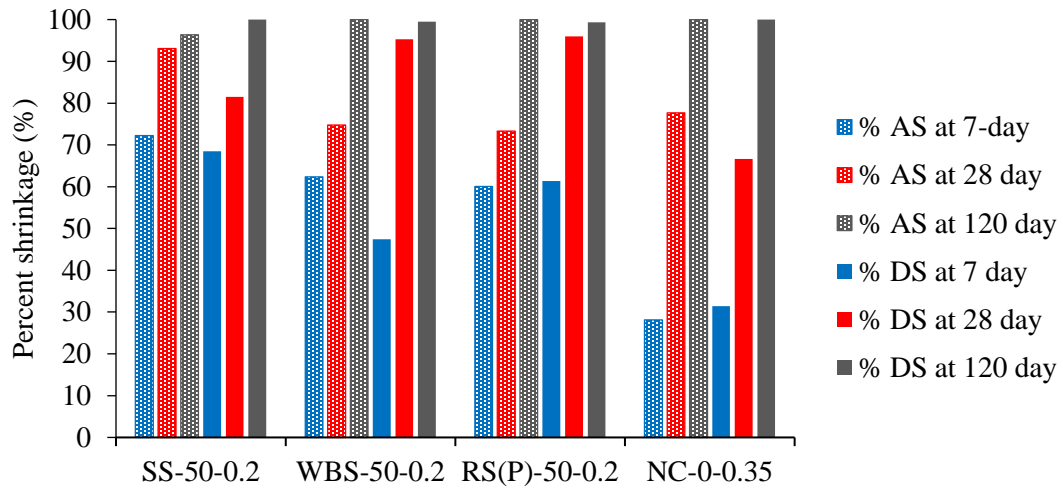

AS – autogenous shrinkage, DS – drying shrinkage.

Figure 14. Percentage of autogenous and drying shrinkage development among mixes with different types of sand.



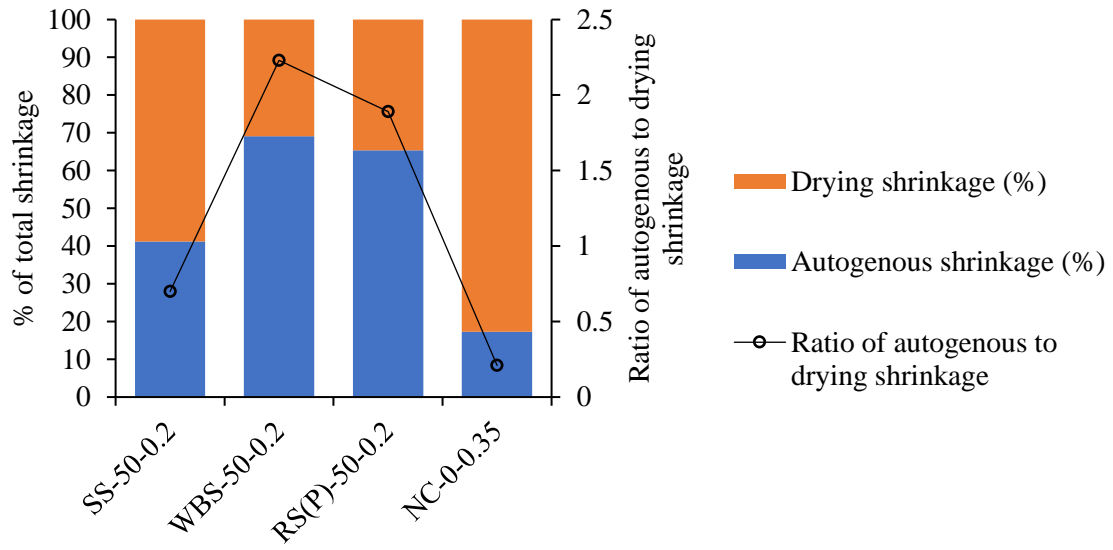



Figure 15. Proportions of autogenous and drying shrinkage at 120 days (different types of sand).

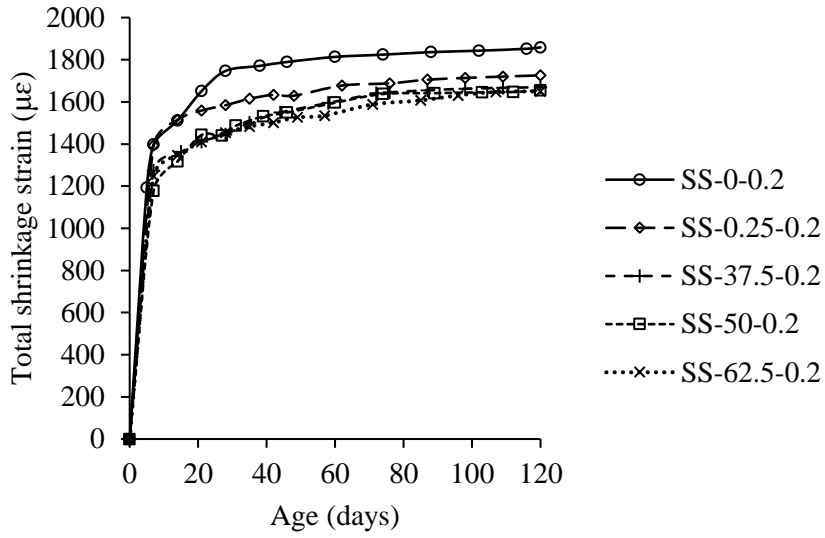

(a)

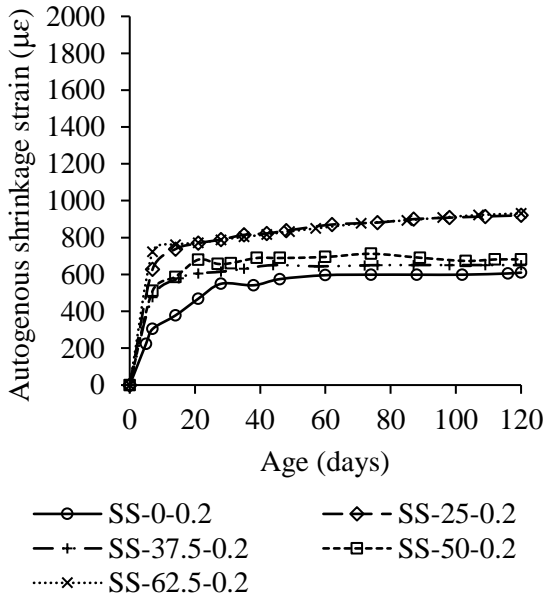


(b)

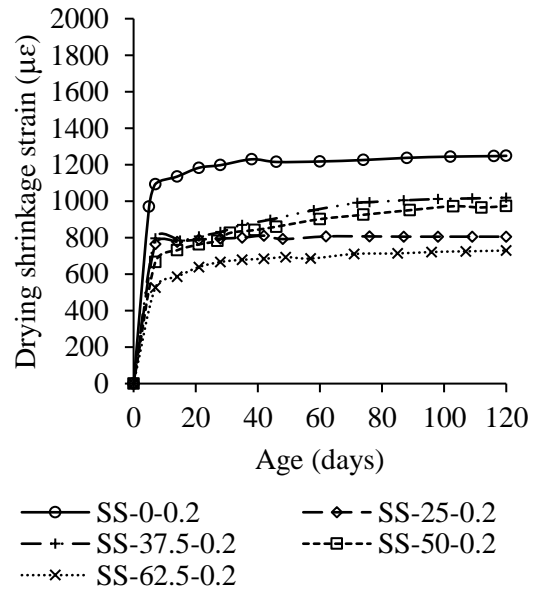


(c)

Figure 16. Influence of OPC replacement on shrinkage of UHPC (a) Total shrinkage, (b) Autogenous shrinkage, (c) Drying shrinkage.

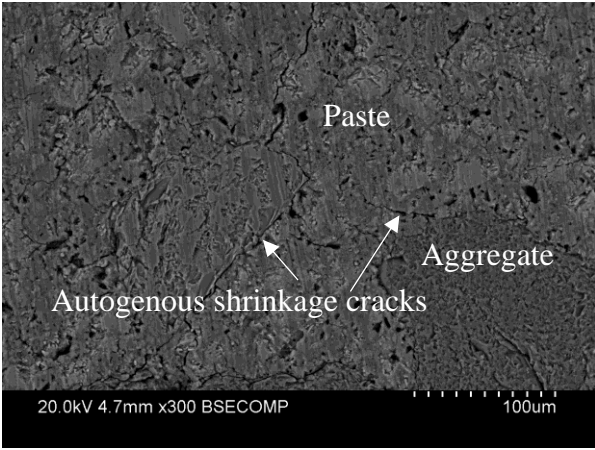


(a)

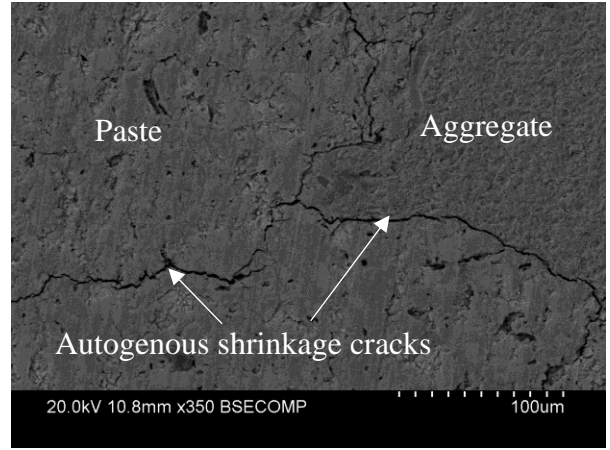

(b)

Figure 17. Autogenous shrinkage cracks in the microstructure of UHPC (a) 100% OPC, (b) 25% OPC replaced by slag.

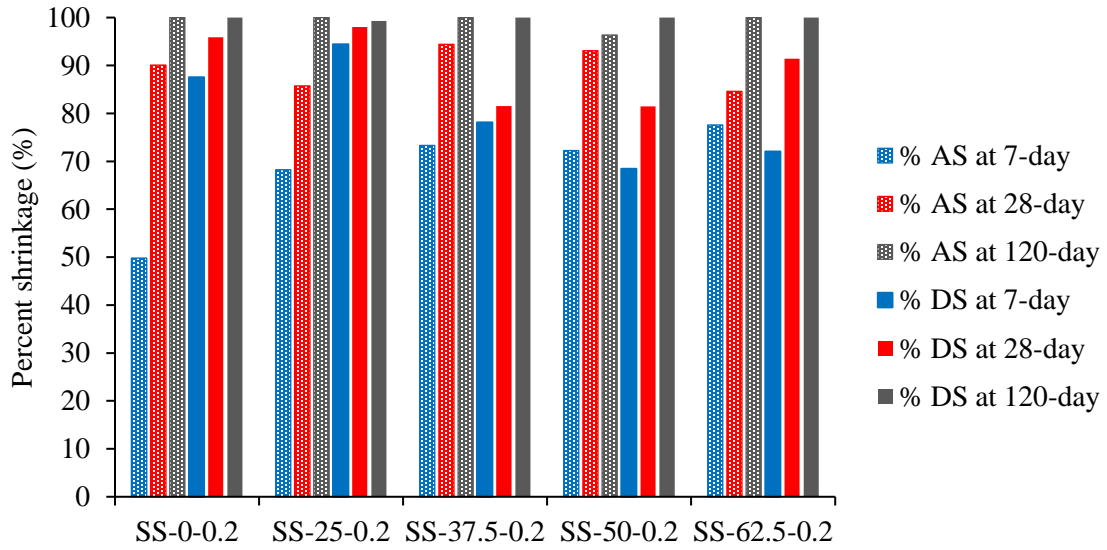

AS – autogenous shrinkage, DS – drying shrinkage.

Figure 18. Percentage of autogenous and drying shrinkage development among mixes with different OPC replacement.



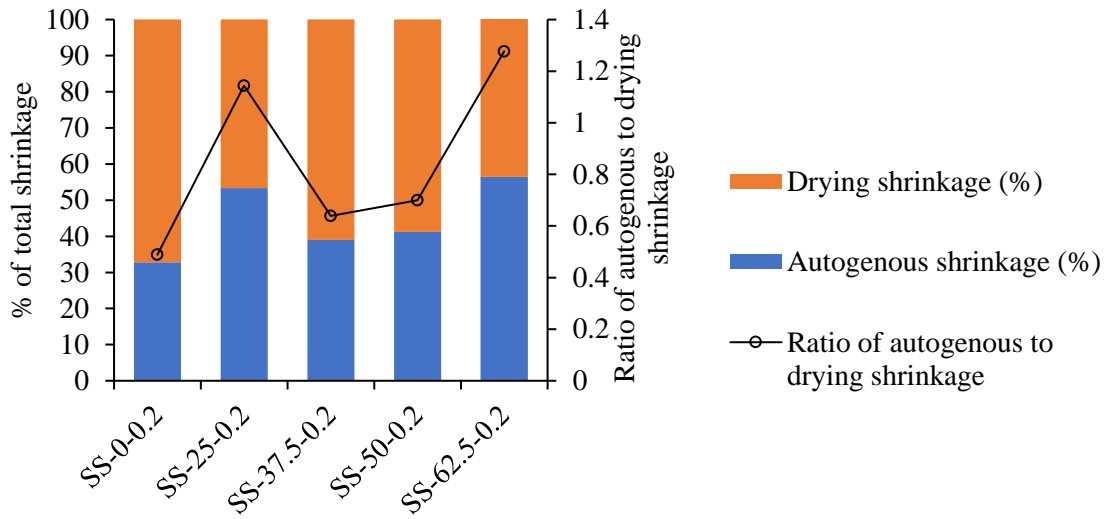



Figure 19. Proportions of autogenous and drying shrinkage at 120 days (percentage of OPC replacement).

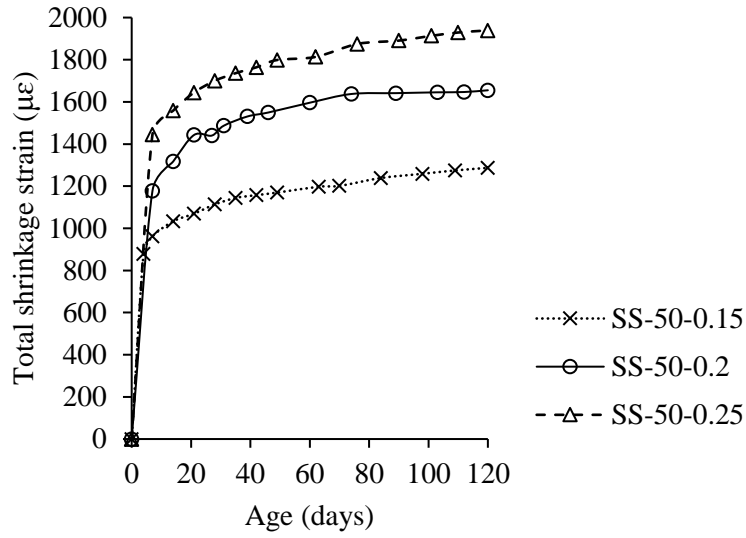

(a)

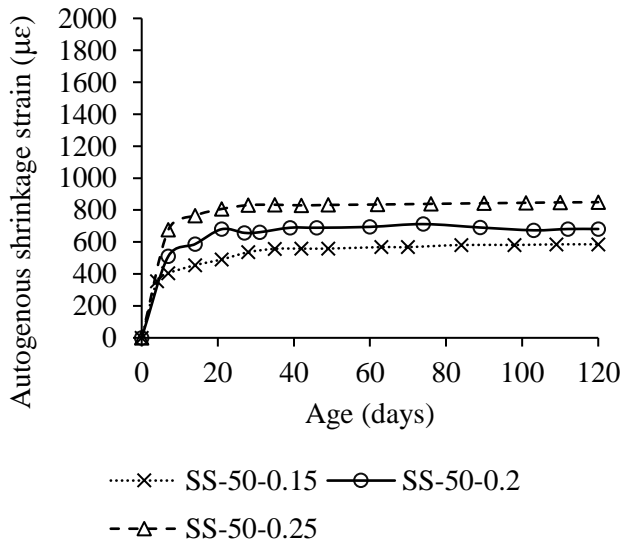


(b)

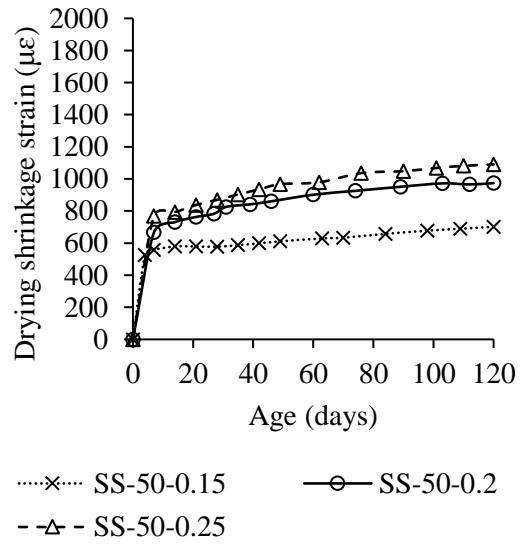

(c)

Figure 20. Influence of water-to-binder ratio on shrinkage of UHPC (a) Total shrinkage, (b) Autogenous shrinkage, (c) Drying shrinkage.

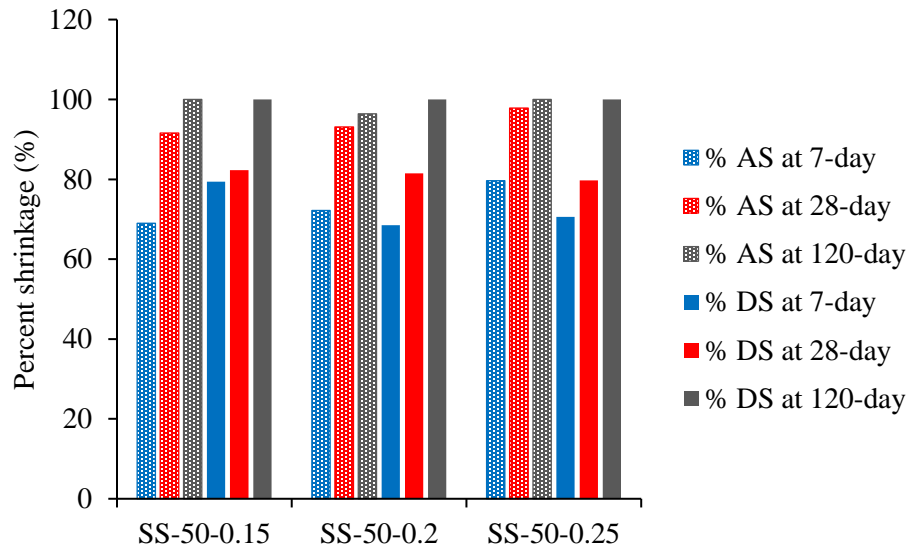

AS – autogenous shrinkage, DS – drying shrinkage.

Figure 21. Percentage of autogenous and drying shrinkage development among mixes with different water to binder ratio.

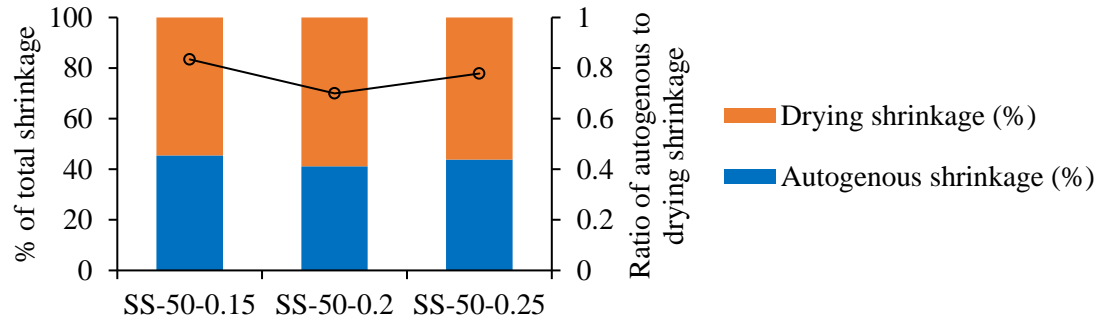


Figure 22. Proportions of autogenous and drying shrinkage at 120 days (water to binder ratio).

Figure captions

Figure 1. Preparation and modification of sea sand (a) Impurities in sea sand, (b) sea sand after processing.

Figure 2. Particle size distribution curves of different sand aggregates (cumulative passing).

Figure 3. SEM images of different sand particles and SCMs (a) Sea sand, (b) washed beach sand, (c) river sand, (d) ground slag, (e) silica fume.

Figure 4. (a) Heat flow and (b) cumulative heat captured in an isothermal condition in the first 72 hours of hydration.

Figure 5. Comparison of workability of fresh UHP-SWSSC (by flow table test) based on (a) percentage of OPC replacement, (b) water to binder ratio, (c) different sand types.

Figure 6. Effect of seawater and sea sand as mixing water and aggregate (tap water curing).

Figure 7. Effect of OPC replacement on cube compressive strength of UHP-SWSSC (tap water curing).

Figure 8. Effect of OPC replacement on cube compressive strength of UHP-SWSSC (seawater curing).

Figure 9. Effect of water to binder ratio on cube compressive strength (seawater curing).

Figure 10. Cross-sections of UHP-SWSSC with different water to binder ratio (a) SS-50-0.15, (b) SS-50-0.2, (c) SS-50-0.25.

Figure 11. Effect of seawater curing on UHPC (100% OPC) with different aggregate types.

Figure 12. Effect of seawater curing on UHPC (50% OPC replacement) with different aggregate types.

Figure 13. Effect of sand types on shrinkage of UHPC (a) Total shrinkage, (b) Autogenous shrinkage, (c) Drying shrinkage.

Figure 14. Percentage of autogenous and drying shrinkage development among mixes with different types of sand.

Figure 15. Proportions of autogenous and drying shrinkage at 120 days (different types of sand).

Figure 16. Influence of OPC replacement on shrinkage of UHPC (a) Total shrinkage, (b) Autogenous shrinkage, (c) Drying shrinkage.

Figure 17. Autogenous shrinkage cracks in the microstructure of UHPC (a) 100% OPC, (b) 25% OPC replaced by slag.

Figure 18. Percentage of autogenous and drying shrinkage development among mixes with different OPC replacement.

Figure 19. Proportions of autogenous and drying shrinkage at 120 days (percentage of OPC replacement).

Figure 20. Influence of water-to-binder ratio on shrinkage of UHPC (a) Total shrinkage, (b) Autogenous shrinkage, (c) Drying shrinkage.

Figure 21. Percentage of autogenous and drying shrinkage development among mixes with different water to binder ratio.

Figure 22. Proportions of autogenous and drying shrinkage at 120 days (water to binder ratio).

Table 1. Chemical compositions of cementitious materials.

Chemical properties (wt. %)	Portland cement	GGBFS	Silica fume
SiO ₂	19.37	32.13	92.18
Al ₂ O ₃	4.88	13.66	0.09
Fe ₂ O ₃	3.4	0.36	0.01
CaO	63.45	42.56	0.1
MgO	0.88	5.51	0.28
Na ₂ O	0.48	0.31	0.22
K ₂ O	0.37	0.31	0.26
TiO ₂	0.31	0.54	<0.01
SO ₃	2.36	3.24	0.01
P ₂ O ₅	0.06	0.01	0.1
Mn ₃ O ₄	0.05	0.15	<0.01
Loss on ignition (LOI)	4.25	0.95	6.25

Table 2. Chemical compositions of natural seawater.

Ion (in mg/L)	Natural seawater from Malabar, NSW	World average of seawater Teng et al. [29]
F ⁻	10.6	1.3
Cl ⁻	19131	19352
Br ⁻	71.7	67.3
SO ₄ ²⁻	2658	2712
PO ₄ ³⁻	nil	nil
NO ₂ ⁻	nil	nil
NO ₃ ⁻	nil	nil
Li ⁺	0.296	nil
Na ⁺	10691	10784
Mg ²⁺	891.6	1283.7
Al ³⁺	0.112	nil
Si ⁴⁺	0.140	nil
K ⁺	427.4	399.1
Ca ²⁺	419.5	412.1
Fe ²⁺	0.002	nil

Table 3. Chemical compositions of different types of sand.

Chemical properties (wt. %)	Sea sand	Washed beach sand	River sand
SiO ₂	88.80	86.00	95.90
Al ₂ O ₃	0.70	1.00	1.08
Fe ₂ O ₃	0.44	0.28	0.23
CaO	4.58	5.32	0.03
MgO	0.17	0.16	<0.01
Na ₂ O	0.20	0.20	0.01
K ₂ O	0.12	0.35	0.18
TiO ₂	0.06	0.03	0.08
SO ₃	0.04	0.02	<0.01
P ₂ O ₅	0.02	0.02	<0.01
Mn ₃ O ₄	<0.01	<0.01	<0.01
SrO	0.03	0.02	0.04
Loss on ignition (LOI)	4.26	5.05	0.85

Table 4. Physical properties of different types of sand.

Physical properties	Sea sand	Washed beach sand	River sand (natural)	River sand (processed)
Oven dry density (t/m ³)	2.41	2.44	2.51	2.41
SSD density (t/m ³)	2.50	2.51	2.55	2.46
Apparent density (t/m ³)	2.63	2.63	2.62	2.55
Uncompacted bulk density (t/m ³)	1.47	1.42	1.50	1.47
Compacted bulk density (t/m ³)	1.68	1.62	1.76	1.67
Water absorption (%)	3.46	2.95	1.68	2.35
Void (%)	38.94	41.73	40.42	39.04

Table 5. Mixture proportions of materials for UHPC and normal strength concrete.

Mix ID	Replacement of OPC (%)	Aggregate	Mixing water	Water to binder ratio	OPC kg/m ³	Ground Slag kg/m ³	Silica fume kg/m ³	Sand kg/m ³	Coarse aggregate kg/m ³	Water kg/m ³	HRWR kg/m ³
SS-0-0.2	0	Sea sand	Seawater	0.2	1200	0	0	1000	N/A	240	24
SS-25-0.2	25	Sea sand	Seawater	0.2	900	300	0	1000	N/A	240	24
SS-37.5-0.2	37.5	Sea sand	Seawater	0.2	750	300	150	1000	N/A	240	24
SS-50-0.2	50	Sea sand	Seawater	0.2	600	450	150	1000	N/A	240	24
SS-62.5-0.2	62.5	Sea sand	Seawater	0.2	450	600	150	1000	N/A	240	24
SS-50-0.15	50	Sea sand	Seawater	0.15	615	461.3	153.7	1025	N/A	184.5	24.6
SS-50-0.25	50	Sea sand	Seawater	0.25	585.7	439.3	146.4	976.2	N/A	292.9	23.43
WBS-0-0.2	0	Washed beach sand	Tap water	0.2	1200	0	0	1000	N/A	240	24
WBS-50-0.2	50	Washed beach sand	Tap water	0.2	600	450	150	1000	N/A	240	24
RS(P)-0-0.2	0	River sand (processed)	Tap water	0.2	1200	0	0	1000	N/A	240	24
RS(N)-50-0.2	50	River sand (natural)	Tap water	0.2	600	450	150	1000	N/A	240	24
RS(P)-50-0.2	50	River sand (processed)	Tap water	0.2	600	450	150	1000	N/A	240	24
NC-0-0.35	0	Washed beach sand	Tap water	0.35	380	0	0	1102	840	133	1.9

SS – Sea sand, WBS – Washed beach sand, RS(P) – Processed river sand, RS(N) – Natural river sand, NC – Normal strength concrete.

Table 6. Fresh and SSD unit weight of UHPC and normal strength concrete.

Mix ID	Fresh density kg/m ³	SSD density kg/m ³
SS-0-0.2	2400.8	2421.0
SS-25-0.2	2373.3	2392.0
SS-37.5-0.2	2316.8	2335.4
SS-50-0.2	2305.0	2323.0
SS-62.5-0.2	2304.8	2315.8
SS-50-0.15	2308.6	2315.4
SS-50-0.25	2247.5	2264.8
WBS-0-0.2	2392.3	2424.4
WBS-50-0.2	2285.1	2291.2
RS(P)-0-0.2	2379.4	2394.2
RS(N)-50-0.2	2322.2	2338.1
RS(P)-50-0.2	2264.3	2299.1
NC-0-0.35	2252.2	2270.8
SS – Sea sand, WBS – Washed beach sand, RS(P) – Processed river sand, RS(N) – Natural river sand, NC – Normal strength concrete.		

Table 7. Compressive strength of UHPC and normal strength concrete (cube specimens).

Mix ID	Curing water	1 day (MPa)		3 days (MPa)		7 days (MPa)		28 days (MPa)		90 days (MPa)	
		Mean	SD	Mean	SD	Mean	SD	Mean	SD	Mean	SD
SS-0-0.2	TW curing	85.23	1.63	106.33	1.74	113.27	6.00	127.43	0.58	141.13	6.10
	SW curing			102.93	2.96	104.10	2.36	112.20	4.69	124.27	2.70
SS-25-0.2	TW curing	57.01	3.16	99.86	3.35	118.40	3.31	131.35	4.17	144.39	0.59
	SW curing			99.67	2.48	111.66	5.17	117.27	9.48	126.47	2.66
SS-37.5-0.2	TW curing	38.94	1.51	93.40	1.31	117.17	5.15	138.63	7.02	143.23	7.27
	SW curing			91.50	0.78	112.03	0.15	129.00	3.20	130.80	8.52
SS-50-0.2	TW curing	37.28	0.22	91.63	2.50	116.53	1.48	136.80	2.00	146.50	9.90
	SW curing			77.30	1.41	106.30	2.94	124.33	5.92	133.55	3.04
SS-62.5-0.2	TW curing	22.85	1.10	75.60	6.47	107.07	3.00	131.10	5.79	148.15	0.21
	SW curing			80.77	1.76	101.60	3.39	113.07	4.87	139.10	3.67
SS-50-0.15	TW curing	52.43	4.95	91.67	3.88	112.50	0.56	128.05	0.07	140.25	6.86
	SW curing			88.83	9.67	110.83	6.43	122.50	3.80	133.77	1.05
SS-50-0.25	TW curing	21.09	0.67	73.03	1.90	94.43	7.25	124.20	3.01	128.97	2.32
	SW curing			70.89	2.80	90.67	8.14	114.73	7.58	129.05	0.35
WBS-0-0.2	TW curing	48.93	1.51	101.07	1.85	106.97	4.01	116.70	9.35	138.47	1.29
	SW curing			101.59	1.59	101.60	5.31	116.60	4.00	126.47	3.04
WBS-50-0.2	TW curing	28.98	3.74	78.40	4.26	102.33	6.38	129.10	6.21	147.57	2.50
	SW curing			65.83	1.71	93.43	4.40	111.70	9.81	131.80	4.00
RS(P)-0-0.2	TW curing	60.07	0.81	101.68	5.91	121.90	0.14	133.50	0.53	148.30	5.62
	SW curing			99.47	4.90	108.43	8.33	134.97	3.08	134.50	3.31
RS(N)-50-0.2	TW curing	28.78	0.80	76.80	0.80	103.73	8.17	131.53	5.98	142.27	6.82
	SW curing			74.53	1.15	95.97	2.25	113.00	10.65	130.07	1.50
RS(P)-50-0.2	TW curing	33.55	0.56	78.58	3.96	114.30	2.51	133.97	3.75	146.70	4.95
	SW curing			70.45	3.59	96.90	1.13	120.20	5.71	139.23	2.50
NC-0-0.35	TW curing	19.10	0.43	24.40	1.44	30.13	1.41	36.54	0.89	41.20	1.61

SS – Sea sand, WBS – Washed beach sand, RS (P) – Processed river sand, RS (N) – Natural river sand, NC – Normal strength concrete, TW – Tap water, SW – Seawater, SD – Standard deviation.

Table 8. Percentage variation of physical, mechanical and stability properties of different mixes compared to reference UHP-SWSSC.

Mix ID	Variation in Unit weight		Variation in workability	Variation in compressive strength (seawater curing)			Variation in maximum shrinkage		
	Fresh unit weight	28-day unit weight		1-day	28-day	90-day	AS	DS	TS
SS-0-0.2	0%	0%	0%	0%	0%	0%	0%	0%	0%
SS-25-0.2	-1.14%	-1.20%	-12.50%	-33.11%	+4.52%	+1.77%	+50.90%	-35.07%	-7.15%
SS-37.5-0.2	-3.50%	-3.53%	-1.39%	-54.32%	+14.97%	+5.26%	+6.72%	-18.37%	-10.14%
SS-50-0.2	-3.99%	-4.04%	-5.56%	-56.26%	+10.81%	+7.47%	+15.92%	-22.01%	-10.95%
SS-62.5-0.2	-4.00%	-4.34%	-19.44%	-73.19%	+0.77%	+11.94%	+52.64%	-41.60%	-10.67%
SS-50-0.15	-3.84%	-4.36%	-48.61%	-38.48%	+9.18%	+7.64%	-4.05%	-43.80%	-30.76%
SS-50-0.25	-6.38%	-6.45%	0%	-75.25%	+2.26%	+3.85%	+39.18%	-12.70%	+4.33%
WBS-50-0.2	-4.82%	-5.36%	-2.78%	-66.00%	-0.45%	+6.06%	+5.48%	-76.82%	-49.88%
RS(P)-50-0.2	-5.68%	-5.03%	-6.94%	-60.63%	+7.13%	+12.04%	+7.38%	-71.99%	-46.07%
NC-0-0.35	-6.19%	-6.20%	N/A	-77.59%	-67.43%	-66.85%	-80.60%	-54.78%	-63.26%

AS – autogenous shrinkage, DS – drying shrinkage, TS – total shrinkage.

NC-0-0.35 was cured in tap water.

A positive (+) value indicates an increase, and a negative (-) value indicates a decrease.